

Minerva Access is the Institutional Repository of The University of Melbourne

Author/s:

Liu, M;Xie, K;Nothling, MD;Zu, L;Zhao, S;Harvie, DJE;Fu, Q;Webley, PA;Qiao, GG

Title:

Ultrapervious Composite Membranes Enhanced Via Doping with Amorphous MOF Nanosheets

Date:

2021-04-28

Citation:

Liu, M., Xie, K., Nothling, M. D., Zu, L., Zhao, S., Harvie, D. J. E., Fu, Q., Webley, P. A. & Qiao, G. G. (2021). Ultrapervious Composite Membranes Enhanced Via Doping with Amorphous MOF Nanosheets. ACS Central Science, 7 (4), pp.671-680. <https://doi.org/10.1021/acscentsci.0c01711>.

Persistent Link:

<https://hdl.handle.net/11343/278372>

License:

CC BY-NC-ND

Ultrapermeable Composite Membranes Enhanced Via Doping with Amorphous MOF Nanosheets

Min Liu, Ke Xie, Mitchell D. Nothling, Lianhai Zu, Shenlong Zhao, Dalton J.E. Harvie,* Qiang Fu,* Paul A. Webley,* and Greg G. Qiao*



Cite This: *ACS Cent. Sci.* 2021, 7, 671–680



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: Thin-film composite (TFC) polymeric membranes have attracted increasing interest to meet the demands of industrial gas separation. However, the development of high-performance TFC membranes within their current configuration faces two key challenges: (i) the thickness-dependent gas permeability of polymeric materials (mainly poly(dimethylsiloxane) (PDMS)) and (ii) the geometric restriction effect due to the limited pore accessibility of the underlying porous substrate. Here we demonstrate that the incorporation of trace amounts (~ 1.8 wt %) of amorphous metal–organic framework (MOF) nanosheets into the gutter layer of TFC assemblies can simultaneously address these two limitations by the creation of rapid, transmembrane gas diffusion pathways. The resultant PDMS&MOF membrane displayed excellent CO_2 permeance of 10450 GPU and CO_2/N_2 selectivity of 9.1. Leveraging this strategy, we successfully fabricate a novel TFC membrane, consisting of a PDMS&MOF gutter and an ultrathin (~ 54 nm) poly(ethylene glycol) top selective layer via surface-initiated atom transfer radical polymerization. The complete TFC membrane exhibits excellent processability and remarkable CO_2/N_2 separation performance (1990 GPU with a CO_2/N_2 ideal selectivity of 39). This study reveals a strategy for the design and fabrication of a new TFC membrane system with unprecedented gas-separation performance.

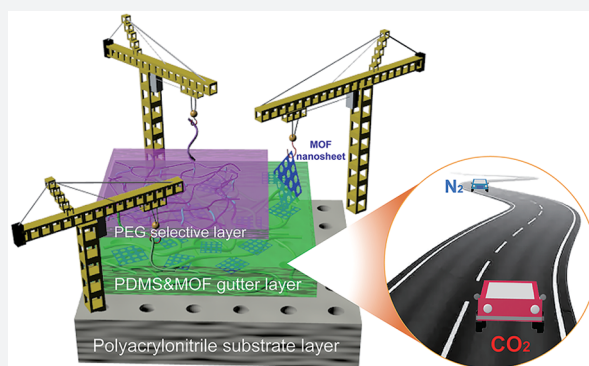

INTRODUCTION

Thin-film composite (TFC) membranes for gas separation, usually consisting of a porous bottom support layer, a highly permeable intermediate gutter layer, and an ultrathin top selective layer, are promising candidates to meet the requirements for high-throughput postcombustion CO_2 capture.^{1,2} A polymeric intermediate gutter layer is essential within a TFC configuration, acting as a multifunctional coating, which can improve the compatibility between the top selective layer and the lower porous support, that is, preventing the penetration of a dilute polymer solution into the porous structure and rendering a smooth surface for coating a top selective layer.³ Frequently, the gutter layer is composed of poly(dimethylsiloxane) (PDMS), which has been the most widespread choice in industry due to its relatively good chemical and thermal stability as well as high gas permeability and excellent processability.⁴ However, the observed permeability of PDMS gutter layers documented in the literature deviates from the theoretical value as the thickness of the PDMS layer is reduced, though the permeability should be independent of film thickness.⁵ As an illustrative example, the observed CO_2 permeability across an ~ 230 nm PDMS layer on a microporous poly(acrylonitrile) (PAN) support is only 660 Barrer, much lower than the intrinsic permeability of PDMS

(ca. 3800 Barrer) at 35 °C.^{4,6} This discrepancy is suggested to be due to various nonequilibrium sorption–desorption effects dominating at the polymer interface as well as morphological changes in the cross-linked polymer network.^{5,7,8} Furthermore, the pore infiltration and the geometric restriction in a TFC membrane assembly resulting from the limited pore accessibility of porous substrates further exacerbate such thickness-dependent permeability.^{9–11} Consequently, these two issues handicap the development of high-performance TFC membranes.

In an effort to address these issues associated with gutter layers, the Park group reported an alternative Teflon (AF2400)-based gutter layer, which displayed excellent CO_2 permeance ($>30\,000$ GPU).⁸ More recently, our group has developed a gutter layer composed of a microporous metal–organic framework (MOF) with a similar gas permeance.^{12,13} However, the expensive Teflon and MOF-based gutter layers

Received: December 23, 2020

Published: March 25, 2021



ACS Publications

© 2021 The Authors. Published by
American Chemical Society

671

<https://doi.org/10.1021/acscentsci.0c01711>
ACS Cent. Sci. 2021, 7, 671–680

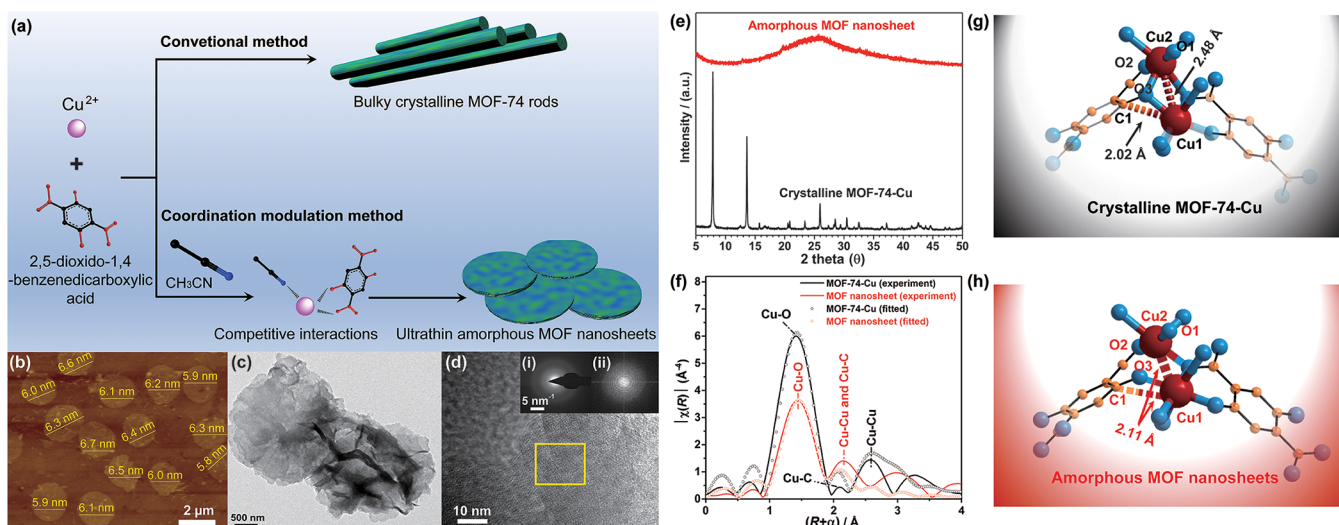


Figure 1. (a) Synthesis of ultrathin amorphous MOF nanosheets by a coordination modulation method. (b) AFM and (c) TEM images of the amorphous MOF nanosheets. The thickness of the amorphous MOF nanosheets is ~ 6 nm measured by AFM (indicated in yellow in (b)). (d) High-resolution TEM image of the amorphous MOF nanosheets. Insets: (i) and (ii) illustrate the selected area electron diffraction and fast Fourier transform patterns of the yellow marked area, respectively. (e) XRD and (f) EXAFS spectra of the amorphous MOF nanosheets and crystalline MOF-74-Cu. The corresponding phase-shifting spectra and fine structural parameters for Cu–O were supplied in Figure S6 and Table S1. (g, h) Proposed chemical bond structures of (g) the crystalline MOF-74-Cu and (h) amorphous MOF nanosheets derived from EXAFS spectra.

have relatively lower flexibility and processability. Furthermore, similar to other highly permeable polymers such as poly(1-(trimethylsilyl)-1-propyne) (PTMSP) and polymers of intrinsic microporosity (PIM),¹⁴ amorphous Teflon also suffers from a physical aging effect, limiting its impact in an industrial setting.¹⁵ The key question here is *Can we enhance the performance of a PDMS gutter layer to the levels achieved for MOF-, Teflon-, or PTMSP-based materials, while simultaneously offsetting the traditional thickness-dependent permeability and geometric restriction of porous substrates, without affecting their high processability?*

Herein, we report a straightforward strategy to dramatically increase the gas permeance of conventional PDMS gutter layers by incorporating trace amounts of novel, ultrathin amorphous MOF nanosheets. We demonstrate that incorporating just ~ 1.8 wt % amorphous MOF nanosheets into an ~ 230 nm PDMS gutter layer can result in an over threefold increase in the gas permeance compared to pristine PDMS of similar thickness without compromising the processability. Investigation via a combined experimental and computational approach reveals a unique mechanism behind the enhancement delivered by amorphous MOF nanosheets through limiting pore infiltration and providing accelerated trans-membrane gas-transport pathways. Such a straightforward doping method is readily generalized to a range of existing TFC materials, providing a powerful new strategy to directly improve the gas-separation performance of current TFC membrane assemblies.

RESULTS AND DISCUSSION

Amorphous MOF Nanosheet Synthesis. MOFs are porous hybrid materials synthesized via linking inorganic metallic nodes and organic ligands through strong coordination bonds in a continuous manner.^{16–18} Most reported MOFs have clear crystalline X-ray diffraction (XRD) patterns as a result of their long-range coordination profiles. However, according to the MOF definition by the International Union of Pure and Applied Chemistry (IUPAC),¹⁹ there is no specific

requirement for long-range order or crystallinity in a MOF structure. As a counterpoint, amorphous MOFs possess the same basic constituents and connectivity of crystalline MOFs and are emerging as functional, porous materials for applications in reversible gas storage and controlled drug delivery.²⁰ As suggested by their name, amorphous MOFs usually display broad, diffuse XRD patterns due to their lack of long-range periodic order caused by the aperiodic arrangements of their constituent atoms. In this work, ultrathin amorphous MOF nanosheets were first synthesized via a simple coordination modulation method. The ligand 2,5-dioxido-1,4-benzenedicarboxylic acid (DOBDC) contains two types of metal-coordinating groups, namely, (i) the two carboxylic acids ($-\text{COOH}$) and (ii) the two hydroxy groups ($-\text{OH}$). As illustrated in Figure 1a, the Cu^{2+} ions can coordinate with a capping molecule (acetonitrile (CH_3CN)) as a neutral Lewis base and DOBDC simultaneously during the synthesis process. Because of the single coordination site of CH_3CN , the framework extension and crystal growth of the MOFs is distorted, resulting in an aperiodic arrangement of the building blocks and anisotropic growth of the MOFs into a two-dimensional (2D) amorphous structure (Figure 1a and Figure S1). In contrast, the preparation of a crystalline analogue (MOF-74-Cu) via a conventional growth method results in rodlike particles (Figure S2).

The prepared amorphous MOF nanosheets appear dislike in shape with a diameter of $\sim 2 \mu\text{m}$ (Figure 1b,c, Figure S3). The thickness of the nanosheets is ~ 6 nm, as determined by atomic force microscopy (AFM, Figure 1b). In addition, no electron reflection was observed when assessing the nanosheets by high-resolution transmission electron microscopy (TEM), confirming the amorphous nature of the prepared MOF nanosheets (Figure 1d). The X-ray diffraction (XRD) pattern of the amorphous MOF nanosheets reveals broad, diffuse peaks in comparison with crystalline MOF-74-Cu,^{21–24} offering further support for their amorphous structure (Figure 1e). Significantly, the amorphous MOF nanosheets display a similar attenuated total reflectance Fourier-transform infrared

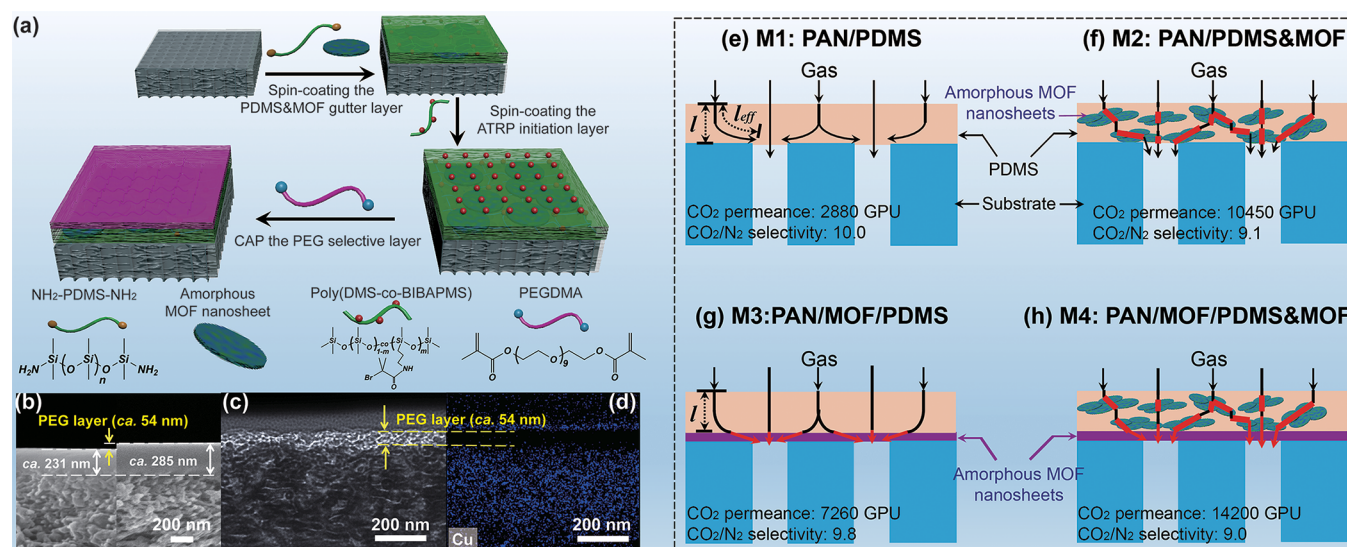


Figure 2. (a) Schematic illustration of the preparation of the TFC membranes by CAP technology. (b) Cross-sectional SEM image of the TFC membrane: (left) PDMS&MOF initiator layer and (right) the final TFC membrane. (c) Cross-sectional TEM image of the TFC membrane and (d) the corresponding Cu K energy-dispersive X-ray spectroscopy image. The yellow line marked areas in (c, d) represent the ultrathin PEG selective layer, and the blue color in (d) indicates the presence of amorphous MOF nanosheets in PDMS. (e) **M1**) Illustration of the geometric restriction effect on the gas diffusion length. A membrane with a gutter layer thickness of l will have an effective diffusion length (l_{eff}) larger than l due to the limited porous accessibility of the substrate. (f–h) Illustration of enhancing gas permeation rate via (f: **M2**) embedding ultrathin amorphous MOF nanosheets into PDMS matrix, (g: **M3**) introducing a porous amorphous MOF nanosheet layer between the PDMS gutter layer and substrate, and (h: **M4**) inserting a porous amorphous nanosheet layer between the PDMS&MOF gutter layer and substrate. The amorphous MOF nanosheet layer was coated onto a PAN substrate by vacuum filtration (CO₂ permeance: 38 000 GPU and N₂ permeance: 40 000 GPU), followed by spin-coating a PDMS or PDMS&MOF layer (2.0 w/v%, 1000 rpm, 10s).

(ATR-FTIR) spectrum to that of the crystalline MOF-74-Cu (Figure S4), suggesting a similar coordination profile between the two morphologies. Specifically, both MOFs display decreased O–H bending and stretching vibration intensities at 1300–1500 cm^{−1} and 2400–3400 cm^{−1}, compared with the pristine DOBDC ligand. This can be attributed to the deprotonation and coordination with Cu²⁺ of the hydroxyl and carboxylate groups of the DOBDC ligand. In addition, the two MOFs showed a weak band at 1450–1500 cm^{−1} and a strong band at 1580–1600 cm^{−1} (red region), indicating the C=C asymmetric and symmetric stretching vibrations of the aromatic ring within the MOFs, respectively. The coordination nature of the amorphous MOF nanosheets was further investigated by ex situ X-ray absorption spectroscopy (XAS). The resultant extended X-ray absorption fine structure (EXAFS) profile of the amorphous MOF nanosheets displayed a similar Cu–O distance to that of crystalline MOF-74-Cu at the main peak of 1.44 Å, along with a decrease in peak intensities (Figure 1f). In addition, significant shifts were observed in the Cu–Cu and Cu–C peaks between amorphous MOF nanosheets and crystalline MOF-74-Cu (Figure 1f). Such decrease and movements can be chiefly attributed to the aperiodic coordination between organic ligands and metal ions within the amorphous MOF nanosheets, leading to shorted adjacent atom distances. In addition, the X-ray absorption near-edge structure (XANES) of the amorphous MOF nanosheets displays decreased and increased peak intensities at ca. 8995 and ca. 8986 eV, respectively (Figure S5), which indicates the partial loss of axial ligands for Cu cations.^{23,25}

Examining the amorphous MOF nanosheets and crystalline MOF-74-Cu using X-ray photoelectron spectroscopy (XPS) (Figure S7) revealed similar coordination properties between the two morphologies, with both exhibiting characteristic

Cu(II) 2p (Cu 2p_{1/2}: 954.8 eV, Cu 2p_{3/2}: 934.9 eV), C 1s (C–C: 285.1 eV, C–O: 287.4 eV, O–C=O: 289.1 eV), and O 1s (C–O–Cu: 532.2 eV and C=O: 533.7 eV) spectra. Such observations are consistent with a previous study by Dietzel et al.,²⁶ where it was suggested that, in the presence of an insufficiently strong base, only the two –COOH groups were deprotonated and coordinated with metal ions to form CPO-26 MOFs with a PtS-type structure. The –OH groups participate indirectly by forming intramolecular hydrogen bonds with the oxygen atoms of the adjacent –COO[−] groups. To further confirm the coordination motif in the obtained amorphous MOF nanosheets, the DOBDC was first dissolved in an equimolar mixture of dimethylformamide-*d*₇ (DMF-*d*₇) and acetonitrile-*d*₃ (CD₃CN-*d*₃) to mimic the experimental deprotonation conditions, resulting in an acidic solution with a pH of 5–6. As shown in Figure S8, only the peak representing the Ar–H is observed in the ¹H NMR spectrum of the mixed solution. This result suggests both the –COOH and the –OH groups were in their deprotonated forms and available for coordination with Cu²⁺ during the MOF synthetic process.^{27,28}

Significantly, both the amorphous MOF nanosheets and their crystalline MOF-74-Cu equivalent exhibit type II N₂ adsorption/desorption isotherms at 77 K, indicating similar structural profiles as well as strong interactions between MOFs and N₂ (Figures S9 and S10). The amorphous MOF nanosheets show a relatively lower surface area (97.9 vs 580.7 m²/g) and total pore volume (0.02 vs 0.69 cm³/g) than those of MOF-74-Cu as expected. This can be attributed to (i) the amorphous nature of the amorphous MOF nanosheets and (ii) the severe aggregation of nanosheets after physical drying,¹³ which cannot present the porous structure of an ultrathin nanosheet observed by TEM (Figure 1c) and scanning electron microscopy (SEM) (Figure S1). Impor-

tantly, the amorphous MOF nanosheets displayed a higher CO₂ adsorption than N₂ at 373 K due to the stronger interactions between CO₂ and Cu²⁺ open metal sites (Figure S11). Examining the amorphous MOF nanosheets by thermogravimetric analysis (TGA) reveals a lower thermal stability in comparison with the crystalline MOF-74-Cu, due to their amorphous character (Figure S12). Interestingly, only the copper-based MOFs displayed a 2D morphology, while other MOFs composed of alternative metal nodes (Mg, Al, Fe, Co, Ni, Zn, Mn, Zr) via the same method exhibited different morphologies (Figure S13). We attribute this difference to the varied coordination profiles of the different metal ions.²⁹

Membrane Preparation and Properties. Following the successful preparation of the amorphous MOF nanosheets, we next sought to examine their impact on gas permeation when doped into a PDMS gutter layer. Briefly, the amorphous MOF nanosheets were mixed with amino-terminated PDMS, which were covalently linked by 1,3,5-benzenetricarbonyl trichloride. This was followed by a spin-coating of the reacted formulation onto pretreated PAN substrates to produce PDMS&MOF gutter layers (Figure 2a). No detectable changes to the infrared spectra were observed between PDMS&MOF and pure PDMS (Figure S14), failing to account for the introduction of amorphous MOF nanosheets. This is attributed to the limited number of specific nanosheet surface contacts compared to the bulk PDMS phase.³⁰ Notably, the resultant gutter layer exhibited low roughness, similar to a pristine PDMS example, indicating an even dispersion of amorphous MOF nanosheets within the PDMS matrix (Figure S15a,b). It is known that many MOFs are not stable in a highly acidic solution, as indicated by the acid–base theory (i.e., strong acids will replace weak acids). However, in the current reaction, the generated HCl molecules have a very low solubility in the employed hydrophobic hexane, limiting their interaction with the amorphous MOF nanosheets. In addition, we also observed some amorphous MOF aggregation after spin-coating via AFM measurements (Figure S15c). This result further demonstrates that the amorphous MOF nanosheets are chemically stable during the spin-coating process.

Unexpectedly, the prepared gutter layer with only ~1.8 wt % amorphous MOF inclusion exhibited a more than threefold increase in CO₂ permeance (10 450 GPU at 1.0 bar, Figure 2f: M2) with a good CO₂/N₂ ideal selectivity of 9.1 in comparison with pristine PDMS gutter layers (2880 GPU, CO₂/N₂ = 10, Figure 2e: M1) of similar thickness. Under further investigation, we found that the enhanced permeance can be attributed to three possible factors: First, the XRD characterization reveals that the embedded amorphous MOF nanosheets can increase the disorder degree of PDMS chain packings (i.e., lowering the local density of PDMS) and thereby increase the free volume within the PDMS layer, favoring an increase in diffusion properties of the formed membrane (Figure S16).³¹ Second, the embedded amorphous MOF nanosheets may mitigate the pore infiltration of PDMS, reducing actual gas transport length. Third, the hierarchical porous structure of the amorphous MOF nanosheets provides a fast diffusion pathway, which can significantly reduce the geometric restriction effect of the composite configuration.^{9,32}

To verify the second and third hypotheses, we conducted two control experiments. First, we coated an ultrathin amorphous MOF nanosheet layer on a PAN substrate via vacuum filtration with a similar mass to that employed in the previous experiment. Then a PDMS or PDMS&MOF layer

was spin-coated on top of the amorphous MOF layer (Figure 2, g: M3 and h: M4). In the case of inserting an amorphous MOF nanosheet layer between the PDMS and substrate (Figure 2g: M3), the resultant membrane showed a CO₂ permeance of 7260 GPU together with a CO₂/N₂ ideal selectivity of 9.8. The increase in CO₂ permeance indicates that the geometric restriction of the porous substrate for CO₂ permeance has been essentially mitigated (or removed) by the fast gas diffusion through the porous amorphous MOF nanosheet layer, in comparison with the pristine PDMS gutter layer (Figure 2e: M1). Further replacing the pristine PDMS layer with a PDMS&MOF layer, the CO₂ permeance reached 14 220 GPU along with a CO₂/N₂ ideal selectivity of 9.0 (Figure 2h: M4). When the separation performance illustrated in Figure 4 is compared, the embedding of amorphous MOF nanosheets into PDMS matrix could substantially enhance the gas-separation performance, indicating both the substrate geometric restriction and the thickness-dependent gas-permeability issues have been substantially resolved.

To further probe these experimental results, a complementary quantitative diffusion simulation study was conducted to probe how the amorphous MOF nanosheets are increasing the membrane permeability.³³ The simulations (detailed further in the Methods section) consider the axi-symmetric diffusion of CO₂ around a prototypical substrate pore and model the permeability of the PDMS&MOF material using a composite resistance-based model that accounts for the aspect ratio of the MOF inclusions. Hence, in the model the (tensor) permeability of the PDMS&MOF material is different in the horizontal (radial) and vertical (axial) directions, capturing in the diffusion modeling some of the geometrical aspects of the included amorphous MOF nanosheet structures. Simulations were conducted both with and without amorphous MOF nanosheet boundary layers.

First, we characterized the pristine substrate, and a surface porosity of ~3.5% along with an average pore size of ~11.5 nm was obtained (Figures S17 and S18). As PDMS suffers from a thickness-dependent gas permeability and pore infiltration, we first simulated the CO₂ permeation of the PAN/MOF/PDMS membrane (Figure 2g: M3). This is because the inserted amorphous MOF nanosheet layer can not only function as fast diffusion lanes to remove the geometric restriction but also prevent the penetration of PDMS into the lower PAN substrate. As a result, the simulated CO₂ permeability of PDMS in the PAN/MOF/PDMS membrane should be the “real” performance of a 230 nm “free-standing” PDMS membrane, which can be further used to simulate the other three membranes. In the first simulation study, the CO₂ permeance of 7300 GPU for the PAN/MOF/PDMS membrane (Figure 2g: M3) was used to determine the CO₂ permeability of the bulk PDMS material. An iteration showed that a permeability of 1660 Barrer for bulk PDMS produced the correct M3 membrane performance, and it was hence used for the bulk PDMS permeability for the other three membrane configurations. For the PAN/MOF/PDMS&MOF (Figure 2h: M4) membrane, it was found that the simulated CO₂ permeance was the same as the tested performance (14 200 GPU) when the aspect ratio of the amorphous MOF inclusions was set at ~5.9 (Figure 3b). The simulated high aspect ratio of the amorphous MOF nanosheets can be attributed to the finite width of the amorphous MOF nanosheets and the constraint that they cannot be perfectly flat within the thin PDMS matrix,

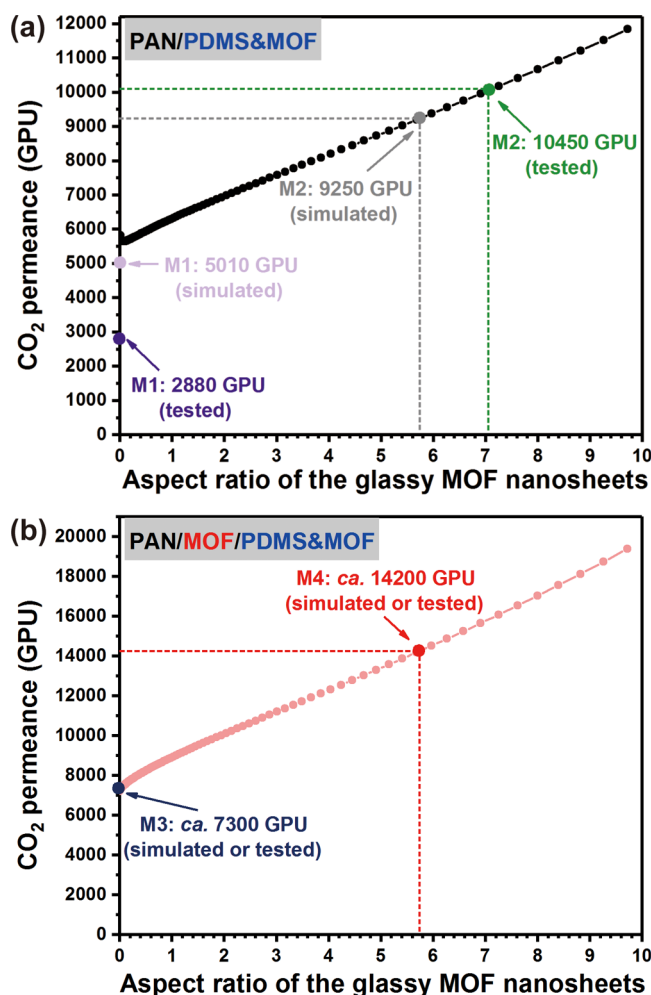


Figure 3. Comparison of tested and simulated CO₂ permeance of (a) M1: PAN/PDMS (with 0 v/v% amorphous MOF nanosheets loading) and M2: PAN/PDMS&MOF, and (b) M3: PAN/MOF/PDMS (with 0 v/v% amorphous MOF nanosheets loading) and M4: PAN/MOF/PDMS&MOF membranes with different amorphous MOF nanosheet aspect ratios in PDMS.

leading to the aggregation or self-folding of amorphous MOF nanosheets in PDMS.

With the diffusion model calibrated using the two &MOF membrane configurations (M3 and M4), the permeance of the remaining two non-&MOF membrane configurations (M1 and M2) were interpreted using the model. Simulating the performance of the PAN/PDMS&MOF membrane (Figure 2f: M2), we found the M2 displayed a CO₂ permeance of 9250 GPU at the same amorphous MOF nanosheet inclusion aspect ratio of 5.9, which is broadly consistent (~11.5% lower) with the measured value (9250 vs 10 450 GPU, Figure 3a). This correspondence suggests that the model is capturing the different diffusion effects caused by the amorphous MOF nanosheet inclusions and amorphous MOF nanosheet layers. The small difference between permeance results for M2 may be attributed to the variation in the self-folding behavior of the amorphous MOF nanosheets or to the morphological changes in the cross-linked polymer network around the amorphous MOF nanosheet inclusions.

While the above three simulated CO₂ permeance results were close to the tested values using a PDMS CO₂ permeability of 1660 Barrer (and amorphous MOF nanosheet

inclusion aspect ratio of ~5.9), the simulated CO₂ permeance of the PAN/PDMS (M1) membrane is much higher than the simulated data (5010 vs 2880 GPU). This can be attributed to the penetration of PDMS into the PAN substrate during the membrane fabrication process, leading to an effectively thicker PDMS gutter layer than that measured by SEM. To quantify the penetration, a further calculation of the pore infiltration length was conducted by considering the resistance of infiltration (eq 1, detailed further in the Supporting Information)

$$\frac{1}{Q_t} = \frac{1}{Q_m} + \frac{l_p}{\phi \times P_m} \quad (1)$$

where Q_t and Q_m are the tested and simulated CO₂ permeance of the PAN/PDMS membrane (M1), respectively, ϕ is the porosity of the PAN substrate, and P_m is the CO₂ permeability of PDMS (1660 Barrer). According to the calculation, the penetration length is ~8.5 nm, which is small compared to the overall thickness of the PDMS layer but contributes significantly to the overall diffusion resistance due to the relatively low porosity of the PAN substrate. Indeed, such a minor penetration caused a 42.5% loss of CO₂ permeance, highlighting the importance of removing the geometric restriction generated from the lower substrate.

We also investigated the type of MOFs and the morphological influence of MOF fillers on gas permeance through PDMS membranes. Of particular note, all of the examined MOFs are nanoparticles. As shown in Figures S19 and S20, MOF-Zr (~30 nm, Figure S13g) and MOF-Al (~50 nm, Figure S13h) nanoparticles were poorly dispersible in hexane, resulting in a lower mass loading in the doped PDMS matrix compared to amorphous MOF nanosheets. The resultant PDMS&MOF-Al and PDMS&MOF-Zr membranes presented a CO₂ permeance of 9700 and 12 800 GPU together with a CO₂/N₂ selectivity of 4.7 and 2.5, respectively. The improved CO₂ permeance together with the decreased CO₂/N₂ selectivity are indicative of an aggregation of the MOF nanoparticles, leading to the formation of defects (Figure S21). In addition, the observed MOF aggregations further indicate the generated HCl has a negligible influence on MOF stability during the PDMS cross-linking process. Considering the high gas-separation performance along with the high processability of the amorphous MOF nanosheets blended PDMS gutter layer, the fabricated membranes (Figure 2f: M2) were further tested under variable gas-separation conditions. Significantly, the PDMS&MOF gutter layer showed a constant CO₂/N₂ separation performance under a pressure between 0.5 and 4.0 bar (Figure 4a). However, an increasing trend of gas permeance along with a loss of gas selectivity was observed under elevated temperatures. This result can be attributed to the well-known plasticization of PDMS chains at high temperatures (Figure 4b). The stability of the prepared PDMS&MOF gutter layer in the presence of water vapor (100% relative humidity) was also examined, revealing a 16% loss of CO₂ permeance together with a 21% loss of CO₂/N₂ selectivity due to the competitive sorption effect of H₂O (Figure 4c). Importantly, the PDMS&MOF gutter layer recovers its original separation performance after being dried under vacuum, highlighting its high stability toward water vapor.

Interestingly, the PDMS&MOF gutter layer displayed enhanced thermal stability compared to the pristine PDMS

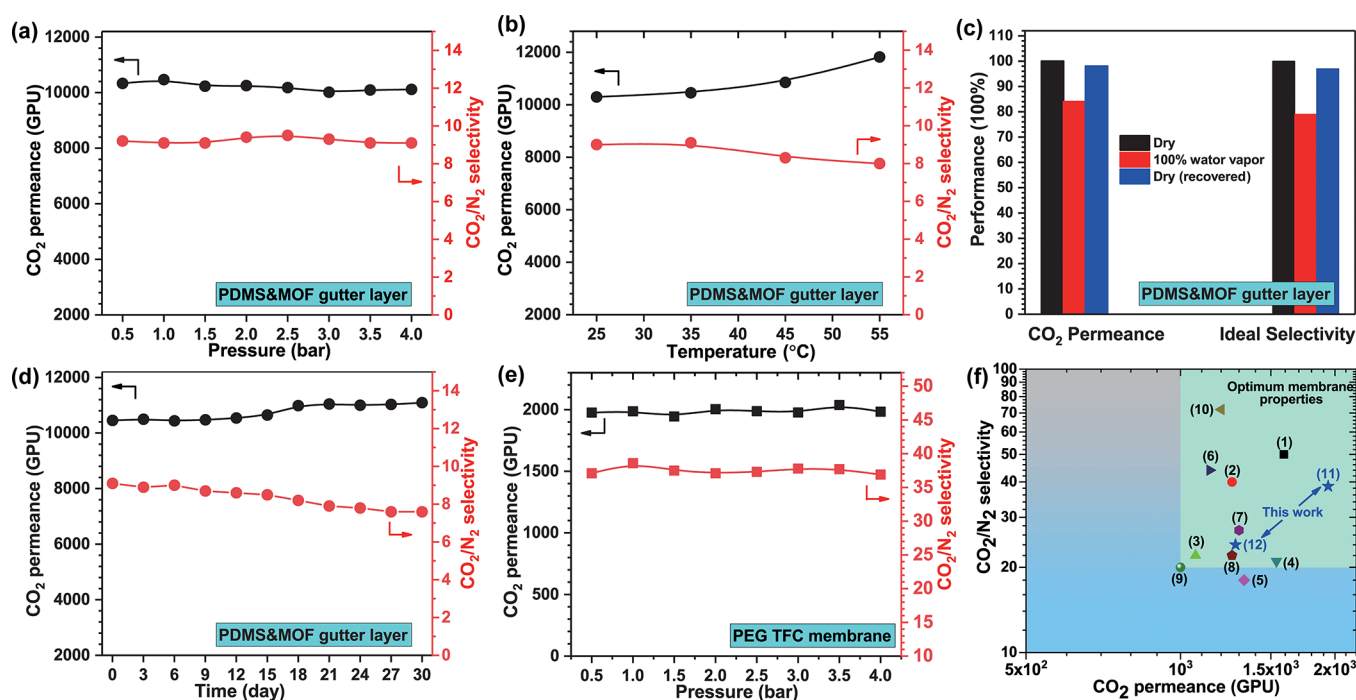


Figure 4. CO₂/N₂ separation performance of PDMS&MOF gutter layer under variable conditions: (a) 0.5–4.0 bar, (b) 25–55 °C, (c) in the presence of 100% water vapor, and (d) long-term stability within 30 d. (e) The CO₂/N₂ separation performance of complete PEG-based TFC membranes under a pressure range of 0.5–4.0 bar. (f) The CO₂/N₂ selectivity vs CO₂ permeance plot comparing the performance of the prepared TFC membranes with other state-of-the-art TFC membranes reported in the literature. The region designated as the target performance area for postcombustion CO₂ capture was inferred from Merkel et al.³⁴ Further figure details are summarized in Table 1.

Table 1. Comparison of the CO₂/N₂ Separation Performance of Film Composite Membranes using PDMS as Gutter Layers^a

entry and reference	membrane configuration			operation conditions ^c	CO ₂ permeance (GPU)	CO ₂ /N ₂ ideal selectivity
	selective layer	gutter layer	total thickness ^b (nm)			
(1) <i>Energy Environ. Sci.</i> 2011 , 4, 4656	polyactive	PDMS	130	30 °C	1590	50
(2) <i>Energy Environ. Sci.</i> 2016 , 9, 434	PEG	PDMS	>240	35 °C, 3.5 bar	1260	40
(3) <i>J. Mater. Chem. A</i> 2013 , 1, 13769	Pebax2533/HMA-PEO	PDMS	600	35 °C, 3.5 bar	1070	22
(4) <i>Ind. Eng. Chem. Res.</i> 2016 , 55, 8364	Pebax1657/P1	PDMS	675	35 °C, 3.5 bar	1538	21
(5) <i>J. Membr. Sci.</i> 2016 , 499, 191	Pebax2533/P21–4.3	PDMS	910	35 °C, 3.5 bar	1330	18
(6) <i>Nanoscale</i> 2016 , 8, 8312	PEG/FeDA	PDMS	450	35 °C, 3.4 bar	1140	44
(7) <i>J. Mater. Chem. A</i> 2015 , 3, 14876	Pebax2533/SNP1	PDMS	550	35 °C, 3.4 bar	1000	20
(8) <i>J. Membr. Sci.</i> 2016 , 515, 54	PEG/PEI-SiO ₂	PDMS	350	35 °C, 3.4 bar	1300	27
(9) <i>J. Membr. Sci.</i> 2017 , 535, 350	polyactive/P&MOF	PDMS	>300	35 °C, 3.0 bar	1260	22
(10) <i>ACS Appl. Mater. Interfaces</i> , 2020 , 12, 33196	Pebax1657	PDMS	410	25 °C, 3.0 bar	3300	37
(11) this work	PEG	PDMS&MOF	285	35 °C, 1.0 bar	1990	39
(12) this work*	PEG	PDMS&MOF	285	35 °C, 1.0 bar CO ₂ /N ₂ = 10/90*	1280*	24*

^aThe facilitated transport membranes were excluded. ^bThe total thickness represents the thickness of the selective layer and gutter layer. ^cThe listed work are the results of single gas-separation tests. The results of the mixed gas (CO₂/N₂ = 10/90) separation tests of this work have been marked with *.

counterpart (Figure S22). This result may be attributed to the strong interaction between PDMS and the amorphous MOF nanosheets. Both the CO₂ permeance and CO₂/N₂ ideal selectivity of the PDMS&MOF gutter layer remained constant after being stored in air for two weeks at 35 °C (Figure 4d). However, when the testing time was further extended to three weeks, the CO₂ permeance increased ~10% compared to the initial performance along with a 20% loss of CO₂/N₂ ideal

selectivity. This result can be attributed to the accelerated CO₂-induced plasticization effect in TFC membranes,³⁵ whereby PDMS interchain interactions were disrupted under the solvating effect of polarizable CO₂ molecules, leading to a faster gas permeation and a loss of selectivity. The PDMS&MOF membranes displayed good structural integrity and flexibility, maintaining their original shape and separation performance after being bent to a large degree for one week

(Figure S23). Increasing the mass loading of the amorphous MOF nanosheets in the PDMS layer to ~3.6 wt % resulted in an increased roughness at the air–polymer interface (Figure S13b), along with an increased CO₂ permeance (12 100 GPU) and an attenuated CO₂/N₂ ideal selectivity (CO₂/N₂ = 7.1). This is attributed to the low dispersity and strong aggregation tendency of the amorphous MOF nanosheets in nonpolar solvents, leading to an exposed population of amorphous MOF nanosheets close to the surface. This phenomenon is exacerbated by the use of a three-dimensional MOF nanoparticle as an additive (Figures S18 and S19). Therefore, thoroughly dispersed porous nanosheets in a PDMS matrix are a desirable trait for the preparation of high-permeance PDMS gutter layers.

For economic postcombustion CO₂ capture, a high CO₂ permeance (>1000 GPU) along with good CO₂/N₂ selectivity (>20) are desirable for membrane-based systems.³⁴ In addition, process constraints, such as the low feed pressure (ca. 1 bar), high volume, and low CO₂ concentration (15–16%) of flue gas as well as a high CO₂ removal requirement (50–90%) further challenge the development of viable membrane designs.³⁶ The compression of flue gas to high pressures to assist the membrane permeation should be avoided to conserve the energy cost of such unit processes. For example, ~20% of the produced energy of power plants would be consumed when compressing the feed to a pressure of 5 bar.³⁴ To demonstrate the potential of our approach in a complete TFC membrane assembly for postcombustion CO₂ capture, an integrated TFC membrane was fabricated by growing a polymeric selective layer onto the cross-linked PDMS&MOF gutter layer via a continuous assembly of polymer (CAP) nanotechnology (Figure 2a). The resultant composite membrane was then cut using a focused ion beam (FIB), and the cross-section was imaged using TEM to reveal the morphology of the individual layers (Figure 2c,d). From this analysis, the thickness of the selective layer is determined to be ~54 nm, agreeing well with SEM measurements (Figure 2b).

In single gas-separation tests, the resultant TFC membranes exhibited a CO₂ permeance of 1990 GPU with a CO₂/N₂ ideal selectivity of 39 at 35 °C and feed pressure of 1 bar, positioning this membrane well-inside the target characteristics for postcombustion CO₂ capture (Figure 4e,f, Table 1). Significantly, the prepared TFC membrane maintains this separation performance under a broad feed pressure range between 0.5 and 4.0 bar. Such a dramatic increase in gas permeance is attributed to the decrease in gas permeation resistance of the gutter layer via the amorphous MOF nanosheets incorporation.¹³ A comparison of this performance with TFC membranes incorporating a pristine PDMS gutter layer (1260 GPU, Entry 2, Table 1)⁶ reveals a 58% increase in CO₂ permeance while maintaining a similar CO₂/N₂ selectivity, corresponding to an ~30% decrease in capture cost (~US\$22 vs ~US\$31, Figure S24). In addition, such a capture cost of this newly designed membrane is much lower than those of state-of-the-art TFC membranes (Figure S24). To further validate this design, the fabricated TFC membranes were also examined in a mixed gas-separation (CO₂/N₂ = 10/90) scenario. Because of the lower CO₂ concentration and diffusion, a lower CO₂ permeance of 1280 GPU and CO₂/N₂ permselectivity of 24 was observed, in line with expectations (Figure 6f and Entry 12, Table 1). Such a performance maintains compliance with the economic requirements for

postcombustion CO₂ capture, highlighting the excellent potential of this technology for industrial TFC membrane development.

METHODS

Synthesis of MOFs. Bulk MOF-74-Cu was synthesized using the previously published procedures.²¹ The amorphous MOF nanosheets were synthesized by the coordination modulation method. Typically, DOBDC (36.0 mg) and 30.0 mg of Cu(NO₃)₂·2.5H₂O were dissolved in a glass vial containing a mixed solvent (4.0 mL of DMF and 4.0 mL of CH₃CN). The glass vial was heated at 313 K for 24 h in static conditions. The reaction mixture was decanted by filtration, and the remaining powder was soaked in 30.0 mL of THF at room temperature for 12 h, after which the solvent was decanted and replaced with fresh deionized THF. Then, the solvent was switched to methanol, and the process was repeated. Finally, the amorphous MOF nanosheets solid was collected by filtration and fully desolvated by heating under vacuum at 373 K for 24 h.

Preparation of the MOF/Hexane Solution (0.36 mg/mL). The fully desolvated amorphous MOF nanosheets (30.0 mg) were dispersed into 1.0 L of *n*-hexane and sonicated for 2 h. The resultant mixture was centrifuged at 4000 rpm for 20 min to remove the thicker amorphous MOF nanosheets and afford a transparent green solution (800.0 mL). The green solution was concentrated to 400.0 mL by a rotary evaporation. To determine the concentration of the amorphous MOF nanosheets in hexane, 45.0 mL of the obtained solution was placed in a glass vial and dried in vacuum at 90 °C overnight. The concentration of the amorphous MOF nanosheets (0.36 mg/mL) was determined by comparing the weight changes of the glass vial.

Fabrication of the PDMS&MOF Gutter Layer. NH₂-PDMS-NH₂ (0.2 g, 0.04 mmol, 1 equiv) was dissolved in 10.0 mL of the green amorphous MOF nanosheet solution (2.0% w v⁻¹, solution A). Another solution was prepared by dissolving 7.0 mg of trimesoyl chloride (TMC, 0.0267 mmol) in 0.35 mL of pure *n*-hexane (2.0% w v⁻¹, solution B). The two solutions were mixed for 2 min, and 1.0 mL of the solution was then spin-coated (1000 rpm, 10 s) onto each PAN substrate (19.63 cm², prewetted in deionized water for 60 min by sonication) to prepare the PDMS&MOF gutter layer. Then, 0.35 mL of TMC solution (1.0% w v⁻¹, in *n*-hexane) was added into 10.0 mL of poly(DMS-*co*-BIBAPMS) solution (2.0% w v⁻¹ in *n*-hexane). The mixture (1.0 mL) was spin-coated (1000 rpm, 10 s) on the precoated PDMS&MOF gutter layer to provide the PDMS&MOF initiator layer. Finally, the precoated substrates were dried in vacuum for 24 h (1 mbar). Each of the obtained PDMS&MOF membranes tested the gas separation performance before coating the selective layer.


Fabrication of the PEG Selective Layer. The CAP process on PDMS&MOF-coated PAN substrate was also conducted under activators regenerated by electron transfer (ARGET)-atom transfer radical polymerization (ATRP) conditions. The PAN substrates with a PDMS&MOF initiator layer were immersed in an aqueous solution of CuBr₂ (1 mM), Me₆TREN (TREN = tris(2-aminoethyl)amine) (3 mM), sodium ascorbate (20 mM), and macrocross-linker (poly(ethylene glycol) dimethacrylate (PEGDMA), 200 mM). After the specified reaction time at room temperature, the substrates were removed, washed with DI water, soaked in water (50.0

mL) for 10 min, and then dried in vacuo at 25 °C for 24 h before the gas-separation tests.

Simulation Study. We employed a computation model to simulate steady-state gas diffusion in our designed composite membranes, accounting for the effect of the amorphous MOF nanosheet inclusions within the PDMS substrate using a tensor resistance model. An axisymmetric domain (r^* , z^*) is used to represent the diffusion around a single prototypical pore. Gas enters along the top of the membrane and leaves through the pore. The PAN substrate is impermeable.

As shown in Scheme 1, for membrane configurations M1 and M2, the membrane consists of only the PDMS&MOF

Scheme 1. Illustration of the Membrane Geometries and Boundary Conditions Employed in This Simulation Study. (a) M1 and M2, (b) M3 and M4

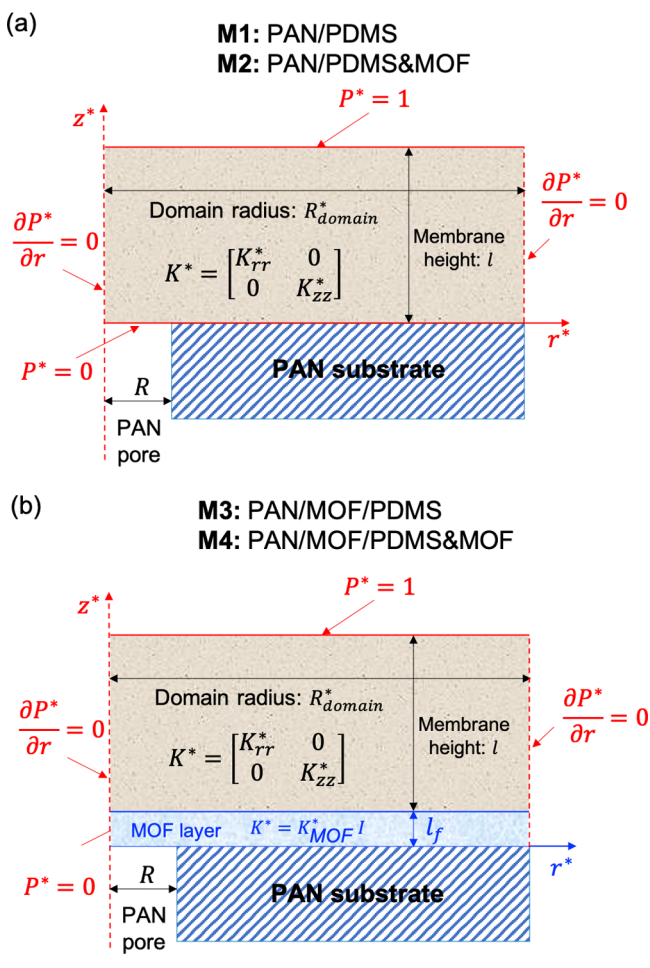

composite (or plain PDMS), while for configurations M3 and M4 the intervening amorphous MOF nanosheet layer of higher permeability is also included. A finite volume method³³ is used to solve the CO₂ transport throughout the membrane via

$$\nabla \cdot \mathbf{r}^* \mathbf{j}^* = 0 \quad (2)$$

where the flux

$$\mathbf{j}^* = -\mathbf{K}^* \cdot \nabla P^* \quad (3)$$

is given by the dot product of the tensor material permeability $\mathbf{K}^*$ and gradient of CO₂ partial pressure P^* that would be in equilibrium with the local concentration. Variables are presented and solved for in a nondimensionalized form


(indicated by an asterisk), with length nondimensionalized by the pore radius R , permeability by the permeability of the bulk PDMS K_{PDMS} , and pressure by the CO₂ partial pressure ΔP applied over the membrane. The height of the composite membrane l is as measured, and the radius of the domain R^*_{domain} is related to the radius of the pore via the porosity of the PAN ϕ such that $R^*_{\text{domain}} = 1/\phi$. The rate of CO₂ transport through the membrane, per membrane surface area and applied pressure (the permeance), is calculated as

$$Q = -\frac{K_{\text{PDMS}} \phi}{\pi R} \int_{\text{pore}} \mathbf{j}^* \cdot \mathbf{k} \, dA^* \quad (4)$$

where the integral is taken over the lower membrane surface at the top of the pore, and $\mathbf{k}$ is the unit vector in the axial direction.

The tensor permeability of the membrane composite $\mathbf{K}^*$ is calculated based on an inclusion model, as illustrated in Scheme 2. Rectangular cuboids of amorphous MOF nano-

Scheme 2. Illustration of the Diffusion Model for the PDMS&MOF Materials Consisting of a Uniform Array of Varying Aspect Ratio Amorphous MOF Nanosheet Inclusions

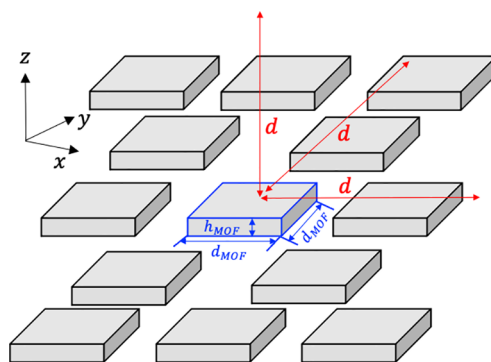

sheets are spaced throughout the model PDMS composite material on a uniform square grid with spacing d . Each inclusion has a height (normal to the membrane) of h_{MOF} and square base dimension of d_{MOF} . One-dimensional resistance theory gives the permeability of the composite in the axial direction as

$$K^*_{zz} = \left[1 - \phi^{1/3} \lambda^{2/3} + \frac{\phi^{1/3} \lambda^{2/3}}{(\phi/\lambda)^{2/3} K^*_{\text{MOF}} + 1 - (\phi/\lambda)^{2/3}} \right]^{-1} \quad (5)$$

and in the radial direction (or any direction parallel to the membrane) as

$$K^*_{rr} = \left[1 - (\phi/\lambda)^{1/3} + \frac{\phi^{1/3}}{(\phi/\lambda)^{2/3} K^*_{\text{MOF}} + \lambda^{1/3} - (\phi/\lambda)^{2/3}} \right]^{-1} \quad (6)$$

where $\phi = h_{\text{MOF}} d_{\text{MOF}}^2 / d^3$ is the volume fraction of amorphous MOF nanosheets in the PDMS composite material, $\phi = h_{\text{MOF}} / d_{\text{MOF}}$ is the aspect ratio of the amorphous MOF nanosheet inclusions, and K^*_{MOF} is the nondimensional permeability of

the amorphous MOF nanosheet material. Geometric considerations limit the inclusion aspect ratio to $\varphi^{-1/2} \gg \varphi$. The 2D axisymmetric permeability tensor within the composite material hence becomes

$$\mathbf{K}^* = \begin{bmatrix} K_{rr}^* & 0 \\ 0 & K_{zz}^* \end{bmatrix} \quad (7)$$

whereas within the intervening amorphous MOF nanosheet layer (for configurations **M3** and **M4**) it is instead $\mathbf{K}^* = K_{\text{MOF}}^* \mathbf{I}$, where $\mathbf{I}$ is the identity tensor.

Parameters used in the simulations were the porosity and pore radius of the PAN substrate, which were measured by SEM and ImageJ software (porosity: $\sim 3.5\%$ and average pore size: ~ 11.5 nm, Figure S15). The volume fraction of the amorphous MOF nanosheets in PDMS was ~ 1.0 v/v%, converted from the mass loading ($\sim 1.8\%$). The thickness (~ 230 nm) of the PDMS gutter layer was determined by SEM (Figure 2b). The CO_2 permeability (294 000 Barrer) of the amorphous MOF nanosheet was obtained from MOF/anodisc composite membranes fabricated by vacuum filtration. A sensitive study found the CO_2 permeability of PDMS and the amorphous MOF nanosheet aspect ratio in PDMS are the main parameters that influence the simulated CO_2 permeance.

CONCLUSIONS

In conclusion, we report a straightforward strategy to reduce the gas transport resistance of PDMS gutter layers by introducing trace amounts of ultrathin amorphous MOF nanosheets into a PDMS matrix. Our MOF-doping strategy mitigates the issues associated with conventional composite membranes, including the thickness-dependent gas permeability of PDMS materials and the geometric restrictions of porous substrates. The prepared PDMS&MOF gutter layer displayed significantly enhanced gas permeance, which can be attributed to (i) increases in the free fractional volume of the PDMS layer following inclusion of the amorphous MOF nanosheets, (ii) a decrease in pore infiltration by PDMS, and (iii) the presence of fast gas transport lanes introduced by the embedded amorphous MOF nanosheets. By employing PDMS&MOF as a gutter layer in a complete TFC assembly, the fabricated membranes exhibited a CO_2 permeance of 1990 GPU with a CO_2/N_2 ideal selectivity of 39 at 35°C feed pressure of 1 bar. This study thus reveals an avenue for the development of scalable, next-generation TFC membranes with high-performance and high processability for industrial gas separation.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acscentsci.0c01711>.

Materials, methods, characterization, SEM images, FTIR, XANES, EXAFS fine structural parameters, ATR-FTIR, AFM, XPS, TGA, ^1H NMR, N_2 and CO_2 adsorption isotherms, XRD, CO_2/N_2 separation performance, MOF dispersion, and membrane images (PDF)

AUTHOR INFORMATION

Corresponding Authors

Dalton J.E. Harvie – Department of Chemical Engineering, The University of Melbourne, Parkville, VIC 3010, Australia; Email: daltonh@unimelb.edu.au

Qiang Fu – School of Civil and Environmental Engineering, University of Technology Sydney, Sydney, NSW 2007, Australia; orcid.org/0000-0002-4012-330X; Email: qiang.fu@uts.edu.au

Paul A. Webley – Department of Chemical Engineering, The University of Melbourne, Parkville, VIC 3010, Australia; Department of Chemical Engineering, Faculty of Engineering, Monash University, Clayton, VIC 3800, Australia; orcid.org/0000-0003-3598-3767; Email: paul.webley@monash.edu

Greg G. Qiao – Department of Chemical Engineering, The University of Melbourne, Parkville, VIC 3010, Australia; orcid.org/0000-0003-2771-9675; Email: gregghq@unimelb.edu.au

Authors

Min Liu – Department of Chemical Engineering, The University of Melbourne, Parkville, VIC 3010, Australia; orcid.org/0000-0003-0201-3553

Ke Xie – Department of Chemical Engineering, The University of Melbourne, Parkville, VIC 3010, Australia; orcid.org/0000-0003-4220-272X

Mitchell D. Nothling – Department of Chemical Engineering, The University of Melbourne, Parkville, VIC 3010, Australia; orcid.org/0000-0002-3259-0047

Lianhai Zu – Department of Chemical Engineering, The University of Melbourne, Parkville, VIC 3010, Australia

Shenlong Zhao – School of Chemical and Biomolecular Engineering, The University of Sydney, Sydney, NSW 2006, Australia

Complete contact information is available at: <https://pubs.acs.org/doi/10.1021/acscentsci.0c01711>

Author Contributions

D.H., Q.F., P.W., and G.Q. conceived the project. M.L. designed the experiments and wrote the manuscript. K.X., M.N., L.Z., and S.Z. contributed to the preparation and characterizations of materials. The manuscript was written with contributions from all authors. All authors have given approval to the final version of the manuscript.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

The authors appreciate the Bio21 Advanced Microscopy Facility for the assistance with material characterization; M.L. acknowledges support from the China Scholarship Council–University of Melbourne Research Scholarship (No. 201606260063). Q.F. acknowledges the Australian Research Council under the Future Fellowship (FT180100312).

REFERENCES

- (1) Baker, R. W.; Low, B. T. Gas separation membrane materials: A perspective. *Macromolecules* **2014**, *47*, 6999–7013.
- (2) Park, H. B.; Kamcev, J.; Robeson, L. M.; Elimelech, M.; Freeman, B. D. Maximizing the right stuff: The trade-off between membrane permeability and selectivity. *Science* **2017**, *356*, eaab0530.

- (3) Galizia, M.; Chi, W. S.; Smith, Z. P.; Merkel, T. C.; Baker, R. W.; Freeman, B. D. 50th anniversary perspective: Polymers and mixed matrix membranes for gas and vapor separation: A review and prospective opportunities. *Macromolecules* **2017**, *50*, 7809–7843.
- (4) Merkel, T.; Bondar, V.; Nagai, K.; Freeman, B.; Pinnau, I. Gas sorption, diffusion, and permeation in poly (dimethylsiloxane). *J. Polym. Sci., Part B: Polym. Phys.* **2000**, *38*, 415–434.
- (5) Firpo, G.; Angeli, E.; Repetto, L.; Valbusa, U. Permeability thickness dependence of polydimethylsiloxane (PDMS) membranes. *J. Membr. Sci.* **2015**, *481*, 1–8.
- (6) Fu, Q.; Kim, J.; Gurr, P. A.; Scofield, J. M. P.; Kentish, S. E.; Qiao, G. G. A novel cross-linked nano-coating for carbon dioxide capture. *Energy Environ. Sci.* **2016**, *9*, 434–440.
- (7) Shishatskii, A.; Yampol'skii, Y. P.; Peinemann, K.-V. Effects of film thickness on density and gas permeation parameters of glassy polymers. *J. Membr. Sci.* **1996**, *112*, 275–285.
- (8) Yoo, M. J.; Kim, K. H.; Lee, J. H.; Kim, T. W.; Chung, C. W.; Cho, Y. H.; Park, H. B. Ultrathin gutter layer for high-performance thin-film composite membranes for CO₂ separation. *J. Membr. Sci.* **2018**, *566*, 336–345.
- (9) Kattula, M.; Ponnuru, K.; Zhu, L.; Jia, W.; Lin, H.; Furlani, E. P. Designing ultrathin film composite membranes: The impact of a gutter layer. *Sci. Rep.* **2015**, *5*, 15016.
- (10) Wijmans, J.; Hao, P. Influence of the porous support on diffusion in composite membranes. *J. Membr. Sci.* **2015**, *494*, 78–85.
- (11) Shi, M.; Dong, C.; Wang, Z.; Tian, X.; Zhao, S.; Wang, J. Support surface pore structures matter: Effects of support surface pore structures on the tfg gas separation membrane performance over a wide pressure range. *Chin. J. Chem. Eng.* **2019**, *27*, 1807–1816.
- (12) Xie, K.; Fu, Q.; Xu, C.; Lu, H.; Zhao, Q.; Curtain, R.; Gu, D.; Webley, P. A.; Qiao, G. G. Continuous assembly of a polymer on a metal–organic framework (CAP on MOF): A 30 nm thick polymeric gas separation membrane. *Energy Environ. Sci.* **2018**, *11*, 544–550.
- (13) Liu, M.; Xie, K.; Nothling, M. D.; Gurr, P. A.; Tan, S. S. L.; Fu, Q.; Webley, P. A.; Qiao, G. G. Ultrathin metal–organic framework nanosheets as a gutter layer for flexible composite gas separation membranes. *ACS Nano* **2018**, *12*, 11591–11599.
- (14) Chen, H. Z.; Thong, Z.; Li, P.; Chung, T.-S. High performance composite hollow fiber membranes for CO₂/H₂ and CO₂/N₂ separation. *Int. J. Hydrogen Energy* **2014**, *39*, 5043–5053.
- (15) Yampol'skii, Y. Polymeric gas separation membranes. *Macromolecules* **2012**, *45*, 3298–3311.
- (16) Yaghi, O. M.; O'keeffe, M.; Ockwig, N. W.; Chae, H. K.; Eddaoudi, M.; Kim, J. Reticular synthesis and the design of new materials. *Nature* **2003**, *423*, 705.
- (17) Férey, G. Hybrid porous solids: Past, present, future. *Chem. Soc. Rev.* **2008**, *37*, 191–214.
- (18) Zhuang, L.; Ge, L.; Liu, H.; Jiang, Z.; Jia, Y.; Li, Z.; Yang, D.; Hocking, R. K.; Li, M.; Zhang, L.; et al. A surfactant-free and scalable general strategy for synthesizing ultrathin two-dimensional metal–organic framework nanosheets for the oxygen evolution reaction. *Angew. Chem.* **2019**, *131*, 13699–13706.
- (19) Batten, S. R.; Champness, N. R.; Chen, X.-M.; Garcia-Martinez, J.; Kitagawa, S.; Öhrström, L.; O'Keeffe, M.; Paik Suh, M.; Reedijk, J. Terminology of metal–organic frameworks and coordination polymers (IUPAC recommendations 2013). *Pure Appl. Chem.* **2013**, *85*, 1715–1724.
- (20) Bennett, T. D.; Cheetham, A. K. Amorphous metal–organic frameworks. *Acc. Chem. Res.* **2014**, *47*, 1555–1562.
- (21) Sanz, R.; Martinez, F.; Orcajo, G.; Wojtas, L.; Briones, D. Synthesis of a honeycomb-like Cu-based metal–organic framework and its carbon dioxide adsorption behaviour. *Dalton T.* **2013**, *42*, 2392–2398.
- (22) Ramohlola, K. E.; Monana, G. R.; Hato, M. J.; Modibane, K. D.; Molapo, K. M.; Masikini, M.; Mduli, S. B.; Iwuoha, E. I. Polyaniline-metal organic framework nanocomposite as an efficient electrocatalyst for hydrogen evolution reaction. *Composites, Part B* **2018**, *137*, 129–139.
- (23) Prestipino, C.; Regli, L.; Vitillo, J. G.; Bonino, F.; Damin, A.; Lamberti, C.; Zecchina, A.; Solarì, P.; Kongshaug, K.; Bordiga, S. Local structure of framework Cu(II) in HKUST-1 metallorganic framework: Spectroscopic characterization upon activation and interaction with adsorbates. *Chem. Mater.* **2006**, *18*, 1337–1346.
- (24) Tan, K.; Chabal, Y. J. Interaction of Small Molecules within Metal Organic Frameworks Studied by In Situ Vibrational Spectroscopy. In *Metal-Organic Frameworks*; IntechOpen: 2016; pp 19–36. DOI: 10.5772/64906
- (25) Huang, C.; Dong, J.; Sun, W.; Xue, Z.; Ma, J.; Zheng, L.; Liu, C.; Li, X.; Zhou, K.; Qiao, X.; Song, Q.; Ma, W.; Zhang, L.; Lin, Z.; Wang, T. Coordination mode engineering in stacked-nanosheet metal–organic frameworks to enhance catalytic reactivity and structural robustness. *Nat. Commun.* **2019**, *10*, 2779.
- (26) Dietzel, P. D.; Blom, R.; Fjellvåg, H. Base-induced formation of two magnesium metal–organic framework compounds with a bifunctional tetratopic ligand. *Eur. J. Inorg. Chem.* **2008**, *2008*, 3624–3632.
- (27) Dietzel, P. D.; Morita, Y.; Blom, R.; Fjellvåg, H. An in situ high-temperature single-crystal investigation of a dehydrated metal–organic framework compound and field-induced magnetization of one-dimensional metal–oxygen chains. *Angew. Chem., Int. Ed.* **2005**, *44*, 6354–6358.
- (28) Dietzel, P. D.; Panella, B.; Hirscher, M.; Blom, R.; Fjellvåg, H. Hydrogen adsorption in a nickel based coordination polymer with open metal sites in the cylindrical cavities of the desolvated framework. *Chem. Commun.* **2006**, 959–961.
- (29) Van Vleet, M. J.; Weng, T.; Li, X.; Schmidt, J. R. In situ, time-resolved, and mechanistic studies of metal–organic framework nucleation and growth. *Chem. Rev.* **2018**, *118*, 3681–3721.
- (30) Bachman, J. E.; Long, J. R. Plasticization-resistant Ni₂(dobdc)/polyimide composite membranes for the removal of CO₂ from natural gas. *Energy Environ. Sci.* **2016**, *9*, 2031–2036.
- (31) Islam, M.; Buschatz, H. Assessment of thickness-dependent gas permeability of polymer membranes. *Indian J. Chem. Technol.* **2005**, *12*, 88–92.
- (32) Xie, K.; Fu, Q.; Webley, P. A.; Qiao, G. G. MOF scaffold for a high-performance mixed-matrix membrane. *Angew. Chem., Int. Ed.* **2018**, *57*, 8597–8602.
- (33) Harvie, D. J. E. An implicit finite volume method for arbitrary transport equations. *ANZIAM Journal* **2010**, *52*, 1126–1145.
- (34) Merkel, T. C.; Lin, H.; Wei, X.; Baker, R. Power plant post-combustion carbon dioxide capture: An opportunity for membranes. *J. Membr. Sci.* **2010**, *359*, 126–139.
- (35) Wessling, M.; Lidon Lopez, M.; Strathmann, H. Accelerated plasticization of thin-film composite membranes used in gas separation. *Sep. Purif. Technol.* **2001**, *24*, 223–233.
- (36) D'Alessandro, D. M.; Smit, B.; Long, J. R. D. M. Carbon dioxide capture: Prospects for new materials. *Angew. Chem., Int. Ed.* **2010**, *49*, 6058–6082.