

Minerva Access is the Institutional Repository of The University of Melbourne

Author/s:

Chambers, A;Prawer, S;Ahnood, A;Zhan, H

Title:

Diamond Supercapacitors: Towards Durable, Safe, and Biocompatible Aqueous-Based Energy Storage

Date:

2022-05-20

Citation:

Chambers, A., Prawer, S., Ahnood, A. & Zhan, H. (2022). Diamond Supercapacitors: Towards Durable, Safe, and Biocompatible Aqueous-Based Energy Storage. *Frontiers in Chemistry*, 10, <https://doi.org/10.3389/fchem.2022.924127>.

Persistent Link:

<https://hdl.handle.net/11343/316282>

License:

[CC BY](#)



# Diamond Supercapacitors: Towards Durable, Safe, and Biocompatible Aqueous-Based Energy Storage

Andre Chambers<sup>1</sup>, Steven Prawer<sup>1\*</sup>, Arman Ahnood<sup>2\*</sup> and Hualin Zhan<sup>3\*</sup>

<sup>1</sup>School of Physics, University of Melbourne, Parkville, VIC, Australia, <sup>2</sup>School of Engineering, RMIT University, Melbourne, VIC, Australia, <sup>3</sup>School of Engineering, Australian National University, Canberra, ACT, Australia

## OPEN ACCESS

### Edited by:

Xiaoliang Yu,  
Hong Kong Polytechnic University,  
Hong Kong SAR, China

### Reviewed by:

Yun Zheng,  
Jiangnan University, China  
Jin Zhao,  
Nanjing University of Posts and  
Telecommunications, China

### \*Correspondence:

Steven Prawer  
s.prawer@unimelb.edu.au  
Arman Ahnood  
arman.ahnood@rmit.edu.au  
Hualin Zhan  
hualin.zhan@anu.edu.au

### Specialty section:

This article was submitted to  
Electrochemistry,  
a section of the journal  
Frontiers in Chemistry

Received: 20 April 2022

Accepted: 02 May 2022

Published: 20 May 2022

### Citation:

Chambers A, Prawer S, Ahnood A and  
Zhan H (2022) Diamond  
Supercapacitors: Towards Durable,  
Safe, and Biocompatible Aqueous-  
Based Energy Storage.  
Front. Chem. 10:924127.  
doi: 10.3389/fchem.2022.924127

Durable and safe energy storage is required for the next generation of miniature bioelectronic devices, in which aqueous electrolytes are preferred due to the advantages in safety, low cost, and high conductivity. While rechargeable aqueous batteries are among the primary choices with relatively low power requirements, their lifetime is generally limited to a few thousand charging/discharging cycles as the electrode material can degrade due to electrochemical reactions. Electrical double layer capacitors (EDLCs) possess increased cycling stability and power density, although with as-yet lower energy density, due to quick electrical adsorption and desorption of ions without involving chemical reactions. However, in aqueous solution, chemical reactions which cause electrode degradation and produce hazardous species can occur when the voltage is increased beyond its operation window to improve the energy density. Diamond is a durable and biocompatible electrode material for supercapacitors, while at the same time provides a larger voltage window in biological environments. For applications requiring higher energy density, diamond-based pseudocapacitors (PCs) have also been developed, which combine EDLCs with fast electrochemical reactions. Here we inspect the properties of diamond-related materials and discuss their advantages and disadvantages when used as EDLC and PC materials. We argue that further optimization of the diamond surface chemistry and morphology, guided by computational modelling of the interface, can lead to supercapacitors with enhanced performance. We envisage that such diamond-based supercapacitors could be used in a wide range of applications and in particular those requiring high performance in biomedical applications.

**Keywords:** diamond, supercapacitor, bioelectronic device, computational modelling, stability, large voltage window, biocompatible, aqueous electrochemical capacitor

## SUPERCAPACITORS AND THE ALLURE OF DIAMOND

Supercapacitors are a type of energy storage device which have been the focus of intense research over the past decades, having the potential to address the limitations in power density and lifetime of current rechargeable battery technology (Simon and Gogotsi, 2008). While high-energy-density rechargeable batteries operate via relatively slow reversible electrochemical reactions, supercapacitors store energy through electrostatic absorption/desorption and/or fast Faradaic mechanisms at the electrode-electrolyte interface. They thus offer higher power densities, i.e., delivering sufficient energy in a short time, shorter charging/discharging rates, and increased cycling stability. On the other hand, supercapacitors generally exhibit intermediate energy densities

between rechargeable batteries and conventional double plate capacitors, and so are currently best suited for applications requiring short bursts of high power. These include hybrid transportation, regenerative braking, portable and wearable electronics, and medical applications (Sinha and Kar, 2020).

Supercapacitors are generally classified into electrochemical double layer capacitors (EDLCs) and pseudocapacitors (PCs). While EDLCs store energy through electrostatic absorption of ions at the electrode-electrolyte interface, PCs utilize fast Faradaic mechanisms (redox reactions) to store energy. The absence of redox reactions in EDLCs leads to high cyclic stability but, due to the screening-affected electrostatic absorption, their energy density is limited. The two key performance metrics for supercapacitors are the energy (E) density and power (P) density. PCs based on materials such as conducting polymer and transition metal oxides typically possess a significantly greater E density (exceeding 100 Wh kg<sup>-1</sup>) compared to EDLCs such as activated carbon or graphene (on the order of 5–10 Wh kg<sup>-1</sup>), but often exhibit lower P density and poorer stability (Yu et al., 2018a). In the broader area of supercapacitor research, PCs are becoming favored over EDLCs because of this superior E density; however, EDLCs are still considered for small scale but high-power applications. The optimization of E and P densities relies on an electrode material with a large specific surface area (SSA), high porosity, high stability and conductivity. One must also consider the choice of electrolyte, with high conductivity, ion sizes that match the electrode pore sizes, and a wide electrochemical potential window (Sinha and Kar, 2020; Yu et al., 2021).

In particular, the advantage of a wide electrochemical potential window in aqueous electrolytes directly affects the supercapacitor performance, as both the E and P density are proportional to the square of the potential window (Gao and Nebel, 2016). This window can be widened by using ionic liquids, or organic and “water-in-salt” electrolytes (for example [EMIM][BF<sub>4</sub>], TEABF<sub>4</sub>/CAN, and LiTFSI, respectively); however, many of these chemicals are flammable or toxic (Martínez-Casillas et al., 2019). Highly toxic electrolytes present a significant health hazard for biomedical applications even if hermetically sealed, and so safer aqueous electrolytes are preferred (Raravikar et al., 2017). Aqueous electrolytes also have high conductivity at room temperature enabling higher P densities, while are generally less expensive than organic electrolytes or ionic liquids (Simon and Gogotsi, 2013; Gao and Nebel, 2016; da Silva et al., 2018). However, the potential window of conventional supercapacitor materials such as activated carbon in aqueous electrolytes is limited to approximately 1.2 V (–0.4 V to +0.8 V vs. SHE at pH = 7) (Kim et al., 2014). If this voltage is exceeded, oxygen and hydrogen evolution reactions take place, leading to the compositional change of the electrolyte and the corrosion of the electrode material (Keskinen et al., 2012; Wang et al., 2020a).

Diamond – particularly boron or nitrogen doped conductive diamond – has been viewed favorably as a supercapacitor

electrode material primarily for its potential to address this issue, possessing a wide electrochemical potential window of up to 3.5 V in aqueous electrolyte to allow higher operation voltages (Gao and Nebel, 2016; Yu et al., 2017; Wang et al., 2020a). While diamond is not yet widely employed due to the relatively high cost and difficulty in processing (Siuzdak and Bogdanowicz, 2018; Yu et al., 2021), it nevertheless has attracted interest for its wide potential window and other excellent properties. For example, diamond is durable and biocompatible, making it suitable for long-term biomedical applications such as high capacitance neural interfaces (Hébert et al., 2014; Garrett et al., 2016; Tong et al., 2016; Siuzdak and Bogdanowicz, 2018; Wang et al., 2020a; Falahatdoost et al., 2021). Diamond also possesses high resistance to biofouling (Trouillon and O’Hare, 2010), and has demonstrated high capacitance in saline solution (Falahatdoost et al., 2021). Moreover, diamond is stable in corrosive chemicals such as nitric or sulfuric acid (Hoffmann et al., 2010), and is resistant to degradation through electrochemical oxidation in contrast to other sp<sup>2</sup> carbon materials (Castanheira et al., 2014; Gao and Nebel, 2016). These properties suggest the use of diamond in surgically implantable supercapacitors, which are attractive power sources for biomedical devices due to high power density, long lifespan, and small dimensions (Chae et al., 2017; Sim et al., 2018; Liu et al., 2021). Diamond-based supercapacitors are able to use safer aqueous electrolytes while retaining an extended potential window, or could possibly even use the physiological electrolyte itself, as has been done previously with other materials [see (Chae et al., 2017; Raravikar et al., 2017; Sim et al., 2018)].

Here, we present our perspective on the current progress and challenges in the development of diamond-based supercapacitors. We argue that while existing diamond-based materials do not have the highest capacitance or energy storage compared with other materials, they nevertheless are well-suited to specialized applications, such as aqueous-based supercapacitors in biomedical electronics. In addition, we suggest diamond could be used in composite-material supercapacitor devices to enhance the electrochemical and environmental stability of existing PC materials. To further optimize diamond-based electrodes for these applications, we propose that special attention should be paid to both the surface chemistry and morphology of the diamond surface in relation to the chosen electrolyte. In particular, optimization of the nanoporous surface can be assisted by computer modelling of ionic processes within the pores of the electrode.

We have noted several past reviews on current research progress on diamond-based supercapacitors, which focus on summarizing the performance and fabrication methods of diamond-based supercapacitors (Gao and Nebel, 2016; Siuzdak and Bogdanowicz, 2018; Yu et al., 2021). In addition to these reviews, here we focus on the specific impacts of surface chemistry and morphology of the diamond surface, which would provide additional vital insights. Moreover, we discuss the biocompatibility aspect of diamond, which combined with its durability and wide potential window in aqueous electrolytes,

makes it a promising candidate for long-term biomedical applications.

Below we briefly outline current experimental progress in the fabrication and application of diamond-based EDLCs and PCs, highlighting the importance of surface chemistry on device performance. We also discuss device level experimental questions which can be assisted by computational simulations, including the modelling of key parameters such as the capacitance in relation to the morphology of porous surfaces. We examine problems and progress with current modelling techniques for supercapacitors, and how this relates to diamond-based materials. We finally weigh up the advantages and disadvantages of diamond-based supercapacitors and offer our perspective on the future prospects and applications of these devices.

## CURRENT EXPERIMENTAL PROGRESS OF DIAMOND SUPERCAPACITORS


Several different classes of diamond-based materials have been developed for supercapacitor applications. As mentioned above, supercapacitors can be divided into electrical double layer capacitors (EDLCs) and pseudocapacitors (PCs), each requiring different materials and properties. PCs possess generally higher capacitances and E density than EDLCs but often poorer stability and P density (Yu et al., 2015). Diamond-based EDLCs are generally composed of a single diamond material, which has been treated to create a rough or nanoporous surface to increase the electroactive surface area. Diamond-based PCs also benefit from a nanoporous surface structure, but also typically require the fabrication of composite materials with other established PC materials (for example, transition metal oxides or conducting polymers). In addition, for both applications modification of the surface chemistry of diamond plays a significant role in the optimization of the supercapacitor properties.

The fabrication methods of diamond-based electrodes with rough or porous surfaces have been comprehensively discussed in previous works (Yu et al., 2021). Briefly, creation of the rough or porous structure has been achieved through either top-down etching, bottom-up overgrowth methods, annealing, selective etching of composite materials, or repeated seeding and growth steps. The top-down etching method utilizes a hard mask such as a metal or metal oxide (Honda et al., 2000, 2001; Yoshimura et al., 2001), and employs an etching technique; for instance plasma etching (Tong et al., 2016), metal particles etching (Ohashi et al., 2009), reactive ion etching (Kondo et al., 2017), or electrochemical etching (Zeng et al., 2019). The bottom-up overgrowth methods make use of a nanostructured template, over which the diamond is grown. These templates include silicon nanowires (Gao et al., 2015; Gund et al., 2015), porous silicon (Ferreira et al., 2005; Silva et al., 2015), 'black' silicon (May et al., 2016), silica fibers (Petrák et al., 2017; Vlčková Živcová et al., 2018), silica nanospheres (Gao et al., 2014), anodized aluminum oxide (AAO) (Masuda et al., 2001; Aramesh et al., 2014), and

quartz fibers (Kondo et al., 2009). The annealing method applies a high temperature to the diamond in vacuum or an atmosphere of air, pure oxygen, or steam. This has been used to produce onion-like carbon (Portet et al., 2007), or roughened diamond from the etching of graphitic grain boundaries (Ohashi et al., 2011; Kondo et al., 2014; Falahatdoost et al., 2021). The selective etching of diamond composite materials grows diamond embedded in a matrix of sacrificial material such as silicon carbide, which is then removed by a wet chemical etch (Zhuang et al., 2015; Yu et al., 2017). Finally, a porous diamond structure may be created by repeated nanodiamond seeding and chemical vapor deposition growth steps (Wang et al., 2020a). A summary of these fabrication methods is shown in **Figure 1**, as well as the basic elements of a supercapacitor energy storage device. This includes two electrodes at which charge is stored, the charge-carrying electrolyte, a ion-permeable membrane 'separator' to prevent a short circuit, and current collectors connected to an external voltage source.

Diamond has also been combined with conventional PC materials to create diamond-based composite-material PCs. The major advantage of these composite materials is that the PC stability can be improved through using a rigid coating or scaffolding material (Kovalenko et al., 2010; Liu and Li, 2020), while also providing other synergistic effects such as improved P density (Aradilla et al., 2016). The materials used to create diamond-based composites include polymers such as polyaniline (PANI) (Kovalenko et al., 2010; da Silva et al., 2018), polypyrrole (PPy) (Hébert et al., 2015), and poly [3, 4-(ethylenedioxy) thiophene] (PEDOT) (Aradilla et al., 2016); transition metals such as nickel (Shi et al., 2016); and transition metal oxides such as manganese oxide (Yu et al., 2015), nickel hydroxide (Gao and Nebel, 2015), ruthenium oxide (Spătaru et al., 2007), and titanium oxide (Shi et al., 2015). The fabrication methods for these composite materials generally involve either subsequent growth/deposition steps or adding diamond nanoparticles to a polymer synthesis process.

The performance of the diamond-based supercapacitors in past works as measured by gravimetric and areal capacitance are summarized and compared to other conventional EDLC and PC materials in **Table 1**. Here we have selected works to highlight the performance of diamond-based supercapacitors relative to other state-of-the-art materials. It is clear that currently the gravimetric and areal capacitance values are not as yet competitive with established supercapacitor materials such as activated carbon, graphene, and transition metal oxides. Regarding cycling stability, diamond EDLCs exhibit high performance (similar to other carbon materials) (Yu et al., 2021), while the cycling performance of diamond-composite PCs has been shown to improve that of conventional PC materials (Kovalenko et al., 2010; Gao and Nebel, 2015; Aradilla et al., 2016; da Silva et al., 2018). This suggests that currently diamond-based supercapacitors are best suited for long term and low energy requirement applications, such as micro or planar devices as noted in previous works (Gao and Nebel, 2016).

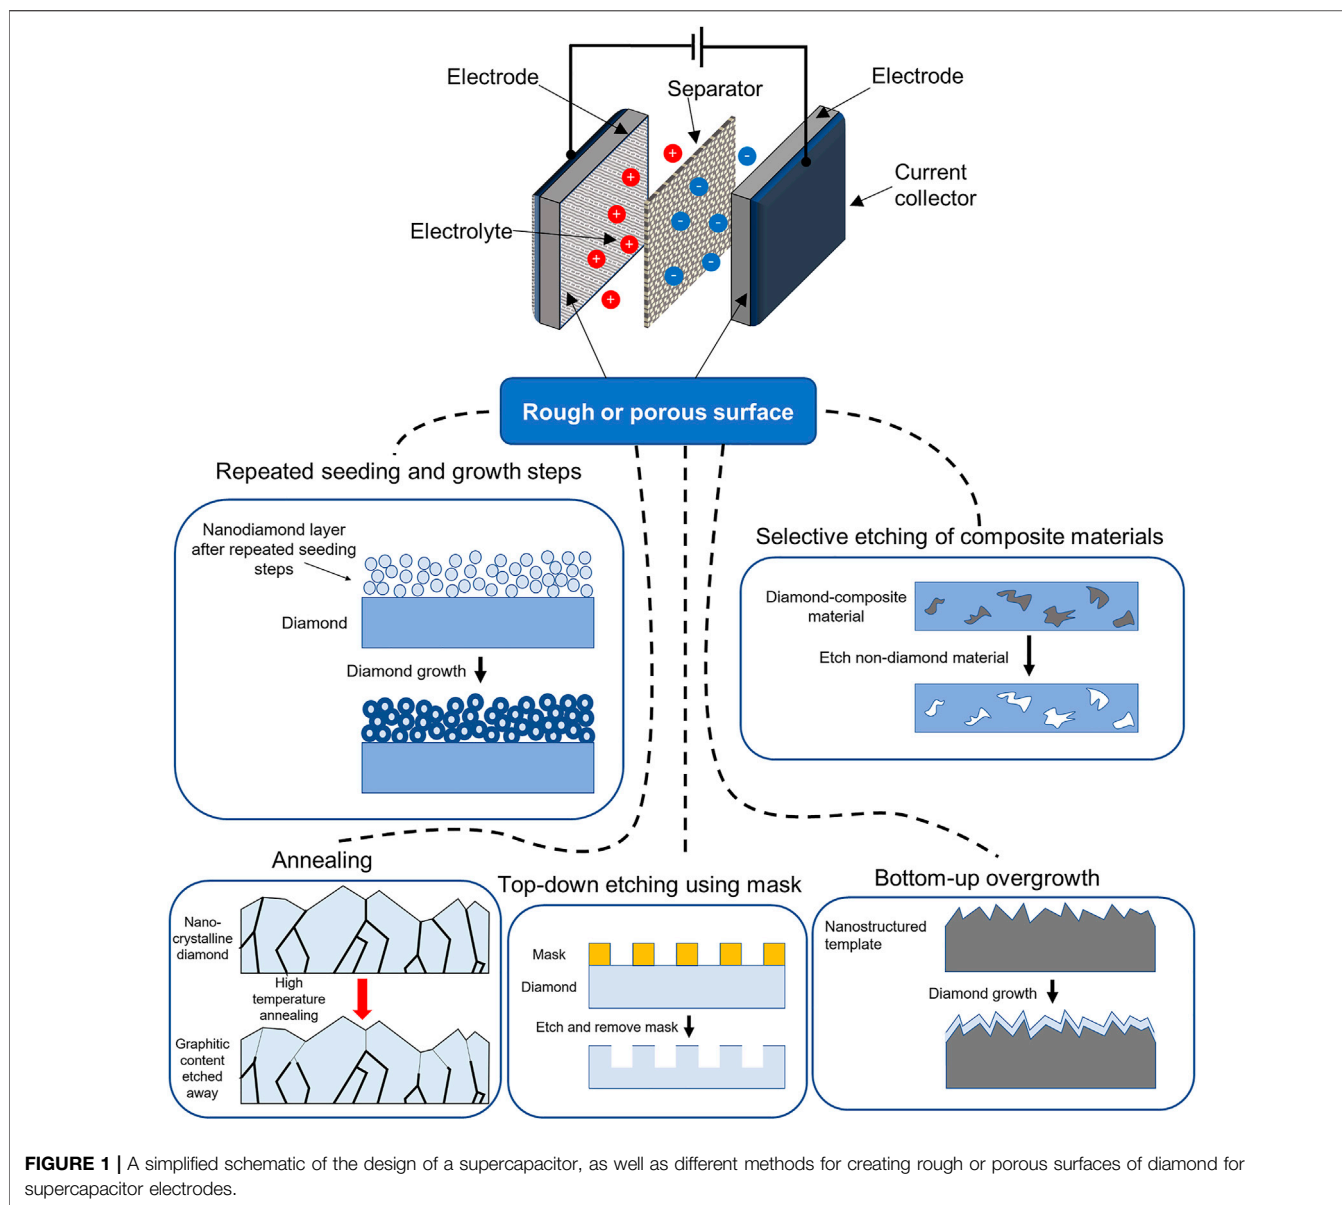

While the fabrication of diamond-based EDLCs and PCs have mainly focused on creating a porous surface morphology, we believe that the surface chemistry is another crucial aspect which should be optimized. Diamond is distinct from other carbon-based electrode materials in its high degree of tunability through surface chemistry, affecting the reactivity, surface wettability, and potential window (Siuzdak and Bogdanowicz, 2018). This is largely due to the semiconducting nature of diamond, where the reaction rate depends on the position of conduction and valence band energy levels relative to the electrochemical potential of redox reactions in the electrolyte. For instance, hydrogen terminated diamond causes upward band bending at the surface so that the valence band overlaps with the energy distribution of the oxygen redox couple, increasing the Faradaic reaction rate and producing surface hole conductivity

(Chakrapani et al., 2007). On the other hand, oxygen terminated diamond exhibits less band bending and so overlaps less with the energy levels of redox species, leading to lower reactivity and greater capacitive behavior (Chakrapani et al., 2007; Chambers et al., 2020; Falahatdoost et al., 2021). This has important implications for diamond composite pseudocapacitors in particular, where the surface chemistry is thought to play a major role in their operational stability (Kovalenko et al., 2010; Yang et al., 2016). The tunable surface chemistry of diamond is thus a major advantage compared with conventional PC materials; with diamond the surface chemistry offers a method of tailoring the surface properties without affecting the mechanical attributes of the electrode.

The surface chemistry of diamond also affects the electrodes' potential window in aqueous solution. For instance, oxygen

**TABLE 1** | A summary of the capacitance and lifetime of aqueous-electrolyte-based capacitors using various materials including diamond.

	Material/thickness of porous layer	Gravimetric capacitance (F g <sup>-1</sup> )/ Areal capacitance (mF cm <sup>-2</sup> )	Lifetime	References
EDLCs				
Diamond-based	BDD network/selective bulk etching of 3 μm film	13.7/5.19 <sup>†</sup>	—	Zhuang et al. (2015)
	N-UNCD/a few nanometers surface etching of 32 μm film	-/28.5	—	Falahatdoost et al. (2022)
Diamond-based (composite)	rGO:ND/drop casting of 300 nm porous film CNF:BDD/3.6 μm layer of CNF grown on BDD substrate	186/- -/138	~100% (1,000 cycles, 2 A g <sup>-1</sup> ) -	Wang et al. (2014) Yu et al. (2018b)
Activated carbon	Fully porous, chemically activated corn residue	575/-	65% (20,000 cycles, -)	Gopiraman et al. (2017)
	Activated carbon cloth with approximately 50 nm porous surface	66.9 <sup>a</sup> /756	>100% (30,000 cycles, 100 mV s <sup>-1</sup> )	Wang et al. (2015)
Graphene-based	Fully porous laminated graphene theoretical limit	550/-	—	Shao et al. (2015)
	Mesoporous 3D printed graphene oxide with 1.25 mm thickness	20.2/101	—	Yun et al. (2019)
PCs				
Diamond-based (composite)	PAni:BDD:CF composite with nanostructured surface	527/-	—	da Silva et al. (2018)
	CNF:BDD/3.6 μm layer of CNF grown on BDD substrate	-/230	—	Yu et al. (2018b)
RuO <sub>2</sub>	Pressurized RuO <sub>2</sub> :carbon powder 100 μm thick RuO <sub>x</sub> N <sub>y</sub> S <sub>z</sub> film	1,390/- -/14,300	93% (4,000 cycles, 2.5 A g <sup>-1</sup> ) 80% (5,000 cycles, 10 mA cm <sup>-2</sup> )	Hong et al. (2014) Patnaik et al. (2020)
MnO <sub>2</sub>	MnO <sub>2</sub> powder	1,380/-	—	Toupin et al. (2004)
	α-MnO <sub>2</sub> /γ-MnO <sub>2</sub> on CNT on yarn	322 <sup>a</sup> /3,540	99% (10,000 cycles, 50 mV s <sup>-1</sup> )	Jeong et al. (2019)

As supercapacitor electrode materials are usually designed for either high gravimetric or areal capacitance, examples of both have been provided for each material. BDD, N-UNCD, rGO, ND, CNF, and CF denote boron-doped diamond, nitrogen-doped ultrananocrystalline diamond, reduced graphene oxide, nanodiamond, carbon nanofiber, and carbon fiber respectively. <sup>a</sup>The quantities marked with <sup>a</sup> were independently calculated using the mass per unit area. All area-dependent quantities refer to the geometric area of the electrodes, not the specific surface area.

terminated diamond is able to undergo larger operation voltages before electrode-degrading reactions begin to occur compared to hydrogen terminated diamond, while it has further been found that fluorine terminated diamond exhibits a potential window in aqueous solutions as large as 5 V (Ferro and De Battisti, 2003). As discussed previously, a wider potential window leads to greater P and E density for a supercapacitor (Simon and Gogotsi, 2008; Yu et al., 2021). It is also worth noting that diamond with sp<sup>2</sup> carbon content exhibits a narrower potential window than pure diamond (Martin et al., 1996), so plasma etching of sp<sup>2</sup> carbon in nanocrystalline diamond is useful for achieving a wider water window. The removal of sp<sup>2</sup> carbon from the diamond surface has previously been suggested for extending the potential window of diamond for supercapacitor applications (Gao and Nebel, 2016); however, we argue that the chemical surface termination should also be tailored for optimal performance.

In the context of biomedical applications, the surface chemistry of diamond also has a significant impact on its

biocompatibility. This property is highly related to the surface wettability, as cells in general are more viable on hydrophilic surfaces (Altankov and Groth, 1994). For instance, the hydrophilic surface of oxygen terminated diamond exhibits greater biocompatibility than the hydrophobic surface of hydrogen terminated diamond (Yang and Narayan, 2019). It is also known that cells prefer rough surfaces, so nanostructured diamond is favorable for cell growth (Yang and Narayan, 2019). Conversely, it has been found that boron-doped diamond cathodically treated in perchloric acid inhibited biofouling (Trouillon and O'Hare, 2010). These are important considerations if diamond-based supercapacitors are to be used in biomedical implants, where cell growth would be encouraged if diamond was used as a device encapsulant, while biofouling resistance would be preferred to allow ions access to the surface of diamond-based electrodes in un-encapsulated devices.

## ASSISTING SUPERCAPACITOR DESIGN THROUGH COMPUTATIONAL MODELLING

In order to evaluate and optimize the performance of diamond-based supercapacitors, computer simulations are often used to model the electrode-electrolyte interface. In this area, both equivalent electrical circuit models and atomistic models are employed, as well as continuum-level simulations.

Equivalent circuit models involve identifying specific charge transfer processes with electronic circuit elements. The models are fitted to data from electrochemical characterization techniques such as cyclic voltammetry (CV), electrochemical impedance spectroscopy (EIS), and galvanostatic charging/discharging (GCD), from which key parameters can be extracted, such as the capacitance and series resistance (Kondo et al., 2009). Equivalent circuit models are much simpler to implement than atomistic models; however, they provide less explanatory power and are not necessarily applicable to nanoporous materials (Pilon et al., 2015; Zhan et al., 2020a).

Atomistic models account for the nanoscale interactions between the nanoporous electrode and ions in the electrolyte, through molecular dynamics (MD) simulation or Monte Carlo simulation (Simon and Gogotsi, 2013). They assist in elucidating nanoscopic ion transport phenomena within the pores of the electrode, to better understand the processes responsible for high supercapacitor performance. For example, past works have investigated the relationship between pore size and capacitance, exploring the complementary contributions of micro and nano sized pores (Eikerling et al., 2004). Furthermore, other works have analyzed different electrode geometries, such as pores, slits, and fibers, as well as film thickness (Chmiola et al., 2010), and mass loading (Lin et al., 2015).

Regarding the optimization of supercapacitor design, a central challenge is a lack of understanding of the nanoconfined charging dynamics in porous surfaces that give rise to capacitance, something which is not trivial to model (Simon and Gogotsi, 2013; Xiao et al., 2020). To address this issue, previous works have applied MD, continuum-level simulations, and machine learning techniques to investigate nonlinear ion dynamics in porous surfaces (Feng and Cummings, 2011; Jiang et al., 2011; Zhan et al., 2020a). It was found that the capacitance has an oscillatory dependence on the pore size (Feng and Cummings, 2011; Jiang et al., 2011), while nonlinear pore-size-dependent confined ion dynamics can lead to capacitive current peaks which may appear Faradaic (Zhan et al., 2020a). Nevertheless, there is yet to be a detailed explanation and prediction for the power and energy density of supercapacitors whose pore sizes are below the size of the ion solvation shell (Simon and Gogotsi, 2013); a question which is still being investigated by these models (Zhan et al., 2020b).


For diamond-based supercapacitors, these models need to account for the specific properties of diamond electrodes. Here, the effect of surface chemistry is significant and must be considered; for example, chemical surface functionalities significantly change the surface wettability. The redox reactions of diamond-based PCs should also be considered in

simulations such as equivalent circuit modelling. Moreover, due to the semiconducting nature of diamond both the space charge region and electrical double layer contribute to the total capacitance of the electrode, and should be incorporated into capacitance calculations, as has previously been done in equivalent circuit models (Falahatdoost et al., 2022). In the context of optimization of the pore geometry in diamond electrodes, it has been previously suggested that anodized alumina oxide (AAO) templates could be used for easily tuning the pore size and shape, film thickness, and mass loading (Gao and Nebel, 2016). This has previously been done to create diamond-like carbon nanotubes (Masuda et al., 2001), and other nanoarchitectures (Aramesh et al., 2014). While current diamond-based supercapacitors have not given particular consideration to the pore geometry, using AAO templates in conjunction with modelling results could provide a tool to enhance the electrode capacitance.

## DISCUSSION

While there has been significant progress in the development of diamond-based supercapacitors, their properties suggest suitability for specific applications. Here it is useful to separately consider diamond-based EDLCs and PCs.

For diamond-based EDLCs, the fundamental disadvantage is that the performance is not currently competitive with state-of-the-art supercapacitor materials in terms of capacitance and energy storage (Yu et al., 2015; Gao and Nebel, 2016). Nevertheless, diamond is attractive for its high durability, biocompatibility, and wide potential window in aqueous media (Gao and Nebel, 2016; Garrett et al., 2016; Wang et al., 2020a). Furthermore, while single crystal diamond involves a high production cost, recent diamond-based supercapacitor electrodes increasingly utilize nanodiamonds or nanocrystalline diamond which can be fabricated at significantly less expense (Williams, 2011; Turcheniuk and Mochalin, 2017). This suggests diamond EDLCs are best suited for small-scale, high-power electronic applications (Gao and Nebel, 2016), such as radiofrequency identification, wireless sensors, or biomedical implants (Gao et al., 2014; Siuzdak and Bogdanowicz, 2018; Wang et al., 2020a). Biomedical applications are also suggested by the diamond electrode's ability to operate in physiological solution (Garrett et al., 2012; Falahatdoost et al., 2021). This approach has previously been demonstrated with other materials and could be used to power small biomedical devices within the body (Chae et al., 2017; Ravavikar et al., 2017; Sim et al., 2018). It has been suggested that supercapacitors can be used in hybrid devices where batteries or energy harvesting devices provide baseload power and supercapacitors can provide peak power (Wang et al., 2020b). For example, a thermoelectric generator in conjunction with a supercapacitor was utilized for powering a pulse oximeter from a person's body heat (Torfs et al., 2006), and a combination of a kinetic energy harvester and supercapacitor was proposed for wireless sensor applications (Olivo et al., 2010). Supercapacitors have also

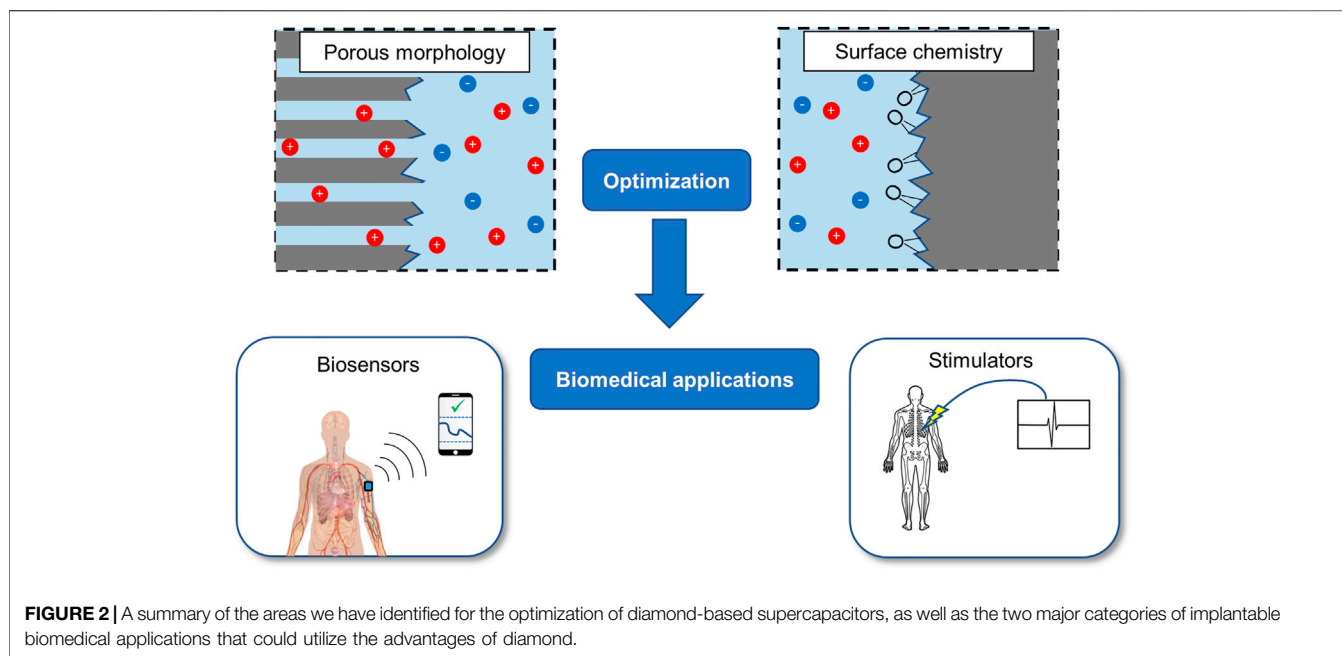

been shown to be useful as standalone power sources for implantable sensors, for instance in monitoring pH levels (Yamada et al., 2004; Pandey et al., 2011). Other applications could include devices for biosensing such as for EEG, ECG, blood pressure, body temperature, pulse, and glucose levels; or devices for stimulation such as artificial retinæ, neurostimulators, and pacemakers (Wang et al., 2020b). Such applications typically require powers of 1–100  $\mu$ W in standby mode, and up to 30 mW in active mode (Patel and Wang, 2010). This requirement is achievable with the power densities of current diamond-based supercapacitor devices (Yu et al., 2021), which have already demonstrated several working prototypes to operate devices such as LEDs, timers, and fans (Cui et al., 2019; Wang et al., 2020b). While the stiffness of diamond precludes it from situations demanding mechanical flexibility, its high durability and biocompatibility provides an advantage over existing supercapacitor materials for long term applications, such as chronic biosensing.

For diamond-based PCs, the greater E density allows for a greater range of applications. Here, the major advantage is the potential for diamond to be used in composite-material PCs with complementary attributes, to enhance for example the stability by providing a rigid scaffold (Kovalenko et al., 2010; Gao and Nebel, 2015; Aradilla et al., 2016; da Silva et al., 2018). Considering biological applications, the biocompatibility of diamond-composite PCs would partly depend on the properties of the non-diamond material. Of the established PC materials, conducting polymers are generally considered biocompatible, with PAni, PPy, and PEDOT:PSS being employed for supercapacitors in biological applications (Sim et al., 2018; Liu et al., 2021; Ramanavicius and Ramanavicius, 2021). In addition, transition metal oxides such as  $\text{MnO}_2$  and  $\text{RuO}_2$  have exhibited

good biocompatibility when the electrode is treated to prevent electrode degradation and ions being eluted into solution (Chae et al., 2017; Wang et al., 2019; He et al., 2020; Shige Wang et al., 2020). Taking this into account, diamond-composite electrodes may assist in the utilization of supercapacitors for long-term biological applications with larger energy requirements. The major drawback of using diamond in these composite electrodes are the added complexity of fabrication (Siuzdak and Bogdanowicz, 2018).

To further improve the performance of diamond-based supercapacitors we believe that additional enhancements can be obtained by fully considering the effect of surface chemistry and utilizing computational simulations to optimize the supercapacitor design for enhanced capacitance and energy storage. In particular, oxygen or fluorine terminated diamond exhibit significantly larger potential windows than as-grown diamond surfaces (Ferro and De Battisti, 2003; Falahatdoost et al., 2021). Furthermore, beyond increasing the surface area of the electrode, computational modelling has found that pore size and shape, film thickness, and mass loading have a large impact on the capacitance and thus E density of the supercapacitor (Simon and Gogotsi, 2013). If the specific surface properties of diamond are taken into account, this modelling can assist in optimizing current diamond electrode fabrication processes and can be tested through adjustable templates such as AAO.

To summarize, diamond-based supercapacitors represent a promising avenue for future energy storage solutions. We believe that diamond is well-suited for biomedical applications as outlined in **Figure 2**; in particular, chronic implantable devices which require intermittent data transfer such as biosensors we believe would benefit from diamond's durability and biocompatibility. On the other hand, diamond-composite PCs

may enhance conventional PCs for cyclic and environmental stability. Both of these types of supercapacitors we argue may benefit from proper consideration of the surface chemistry and design optimization through computational modelling. With these advantages, we believe that diamond-based supercapacitors can make a valuable contribution to energy storage solutions.

## DATA AVAILABILITY STATEMENT

The original contributions presented in the study are included in the article/Supplementary Material, further inquiries can be directed to the corresponding authors.

## REFERENCES

- Altankov, G., and Groth, T. (1994). Reorganization of Substratum-Bound Fibronectin on Hydrophilic and Hydrophobic Materials Is Related to Biocompatibility. *J. Mater. Sci. Mater. Med.* 5 (9), 732–737. doi:10.1007/BF00120366
- Aradilla, D., Gao, F., Lewes-Malandrakis, G., Müller-Sebert, W., Gentile, P., Boniface, M., et al. (2016). Designing 3D Multihierarchical Heteronanostructures for High-Performance On-Chip Hybrid Supercapacitors: Poly(3,4-(ethylenedioxy)thiophene)-Coated Diamond/Silicon Nanowire Electrodes in an Aprotic Ionic Liquid. *ACS Appl. Mat. Interfaces* 8 (28), 18069–18077. doi:10.1021/acsami.6b04816
- Aramesh, M., Fox, K., Lau, D. W. M., Fang, J., Ostrikov, K., Praver, S., et al. (2014). Multifunctional Three-Dimensional Nanodiamond-Nanoporous Alumina Nanoarchitectures. *Carbon* 75, 452–464. doi:10.1016/j.carbon.2014.04.025
- Castanheira, L., Dubau, L., Mermoux, M., Berthomé, G., Caqué, N., Rossinot, E., et al. (2014). Carbon Corrosion in Proton-Exchange Membrane Fuel Cells: from Model Experiments to Real-Life Operation in Membrane Electrode Assemblies. *ACS Catal.* 4 (7), 2258–2267. doi:10.1021/cs500449q
- Chae, J. S., Heo, N.-S., Kwak, C. H., Cho, W.-S., Seol, G. H., Yoon, W.-S., et al. (2017). A Biocompatible Implant Electrode Capable of Operating in Body Fluids for Energy Storage Devices. *Nano Energy* 34, 86–92. doi:10.1016/j.nanoen.2017.02.018
- Chakrapani, V., Angus, J. C., Anderson, A. B., Wolter, S. D., Stoner, B. R., and Sumanasekera, G. U. (2007). Charge Transfer Equilibria between Diamond and an Aqueous Oxygen Electrochemical Redox Couple. *Science* 318 (5855), 1424–1430. doi:10.1126/science.1148841
- Chambers, A., Ahnood, A., Falahatdoost, S., Yianni, S., Hoxley, D., Johnson, B. C., et al. (2020). Near-infrared Excitation of Nitrogen-Doped Ultrananocrystalline Diamond Photoelectrodes in Saline Solution. *Diam. Relat. Mater.* 103, 107720. doi:10.1016/j.diamond.2020.107720
- Chmiola, J., Largeot, C., Taberna, P.-L., Simon, P., and Gogotsi, Y. (2010). Monolithic Carbide-Derived Carbon Films for Micro-supercapacitors. *Science* 328 (5977), 480–483. doi:10.1126/science.1184126
- Cui, D., Li, H., Li, M., Li, C., Qian, L., Zhou, B., et al. (2019). Boron-doped Graphene Directly Grown on Boron-Doped Diamond for High-Voltage Aqueous Supercapacitors. *ACS Appl. Energy Mat.* 2 (2), 1526–1536. doi:10.1021/acsae.8b02120
- da Silva, L. M., de Lima Almeida, D. A., Oishi, S. S., Couto, A. B., and Ferreira, N. G. (2018). Constituent Material Influence on the Electrochemical Performance and Supercapacitance of PANi/diamond/CF Composite. *Mater. Sci. Eng. B* 228, 249–260. doi:10.1016/j.mseb.2017.12.004
- Eikerling, M., Kornyshev, A. A., and Lust, E. (2005). Optimized Structure of Nanoporous Carbon-Based Double-Layer Capacitors. *J. Electrochem. Soc.* 152 (1), E24. doi:10.1149/1.1825379
- Falahatdoost, S., Chambers, A., Stacey, A., Al Hashem, H. N., Nadarajah, A., Praver, S., et al. (2021). Enhanced Electrochemical Capacitance of Nitrogen-Doped Ultrananocrystalline Diamond through Oxygen Treatment. *Appl. Surf. Sci.* 543, 148768. doi:10.1016/j.apsusc.2020.148768
- Falahatdoost, S., Chambers, A., Stacey, A., Praver, S., and Ahnood, A. (2022). Towards Optical Neuromodulation Using Nitrogen-Doped Ultrananocrystalline Diamond Photoelectrodes. *Surfaces Interfaces* 30, 101850. doi:10.1016/j.surfin.2022.101850
- Feng, G., and Cummings, P. T. (2011). Supercapacitor Capacitance Exhibits Oscillatory Behavior as a Function of Nanopore Size. *J. Phys. Chem. Lett.* 2 (22), 2859–2864. doi:10.1021/jz201312e
- Ferreira, N. G., Azevedo, A. F., Beloto, A. F., Amaral, M., Almeida, F. A., Oliveira, F. J., et al. (2005). Nanodiamond Films Growth on Porous Silicon Substrates for Electrochemical Applications. *Diam. Relat. Mater.* 14 (3-7), 441–445. doi:10.1016/j.diamond.2005.01.007
- Ferro, S., and De Battisti, A. (2003). The 5-V Window of Polarizability of Fluorinated Diamond Electrodes in Aqueous Solutions. *Anal. Chem.* 75 (24), 7040–7042. doi:10.1021/ac034717r
- Gao, F., and Nebel, C. E. (2015). Diamond Nanowire Forest Decorated with Nickel Hydroxide as a Pseudocapacitive Material for Fast Charging–Discharging. *Phys. Status Solidi A* 212 (11), 2533–2538. doi:10.1002/pssa.201532131
- Gao, F., and Nebel, C. E. (2016). Diamond-based Supercapacitors: Realization and Properties. *ACS Appl. Mat. Interfaces* 8 (42), 28244–28254. doi:10.1021/acsami.5b07027
- Gao, F., Wolfer, M. T., and Nebel, C. E. (2014). Highly Porous Diamond Foam as a Thin-Film Micro-supercapacitor Material. *Carbon* 80, 833–840. doi:10.1016/j.carbon.2014.09.007
- Gao, F., Lewes-Malandrakis, G., Wolfer, M. T., Müller-Sebert, W., Gentile, P., Aradilla, D., et al. (2015). Diamond-coated Silicon Wires for Supercapacitor Applications in Ionic Liquids. *Diam. Relat. Mater.* 51, 1–6. doi:10.1016/j.diamond.2014.10.009
- Garrett, D. J., Ganesan, K., Stacey, A., Fox, K., Meffin, H., and Praver, S. (2012). Ultra-nanocrystalline Diamond Electrodes: Optimization towards Neural Stimulation Applications. *J. Neural Eng.* 9 (1), 016002. doi:10.1088/1741-2560/9/1/016002
- Garrett, D. J., Tong, W., Simpson, D. A., and Meffin, H. (2016). Diamond for Neural Interfacing: A Review. *Carbon* 102, 437–454. doi:10.1016/j.carbon.2016.02.059
- Gopiraman, M., Deng, D., Kim, B.-S., Chung, I.-M., and Kim, I. S. (2017). Three-dimensional Cheese-like Carbon Nanoarchitecture with Tremendous Surface Area and Pore Construction Derived from Corn as Superior Electrode Materials for Supercapacitors. *Appl. Surf. Sci.* 409, 52–59. doi:10.1016/j.apsusc.2017.02.209
- Gund, G., Dubal, D., Aradilla, D., Mueller-Sebert, W., Bidan, G., Gaboriau, D., et al. (2015). “Diamond-coated Silicon Nanowires for Enhanced Micro-supercapacitor with Ionic Liquids,” in Proceeding of the 2015 International Conference on Industrial Instrumentation and Control (ICIC), Pune, India, May 2015 (IEEE), 1125–1128. doi:10.1109/iic.2015.7150916
- He, S.-B., Balasubramanian, P., Chen, Z.-W., Zhang, Q., Zhuang, Q.-Q., Peng, H.-P., et al. (2020). Protein-Supported RuO<sub>2</sub> Nanoparticles with Improved Catalytic Activity, *In Vitro* Salt Resistance, and Biocompatibility:

## AUTHOR CONTRIBUTIONS

AC wrote the perspective. HZ initiated and revised the perspective. AA and SP revised the perspective. All authors have contributed to and approved the final version of the perspective.

## FUNDING

This work is supported by Australian Research Council grants DP210102750 and LP190100528. AC is supported by an Australian Government Research Training Program (RTP) Scholarship.

- Colorimetric and Electrochemical Biosensing of Cellular H<sub>2</sub>O<sub>2</sub>. *ACS Appl. Mat. Interfaces* 12 (13), 14876–14883. doi:10.1021/acsami.0c00778
- Hébert, C., Mazellier, J. P., Scorsone, E., Mermoux, M., and Bergonzo, P. (2014). Boosting the Electrochemical Properties of Diamond Electrodes Using Carbon Nanotube Scaffolds. *Carbon* 71, 27–33. doi:10.1016/j.carbon.2013.12.083
- Hébert, C., Scorsone, E., Mermoux, M., and Bergonzo, P. (2015). Porous Diamond with High Electrochemical Performance. *Carbon* 90, 102–109. doi:10.1016/j.carbon.2015.04.016
- Hoffmann, R., Kriele, A., Obloh, H., Hees, J., Wolfer, M., Smirnov, W., et al. (2010). Electrochemical Hydrogen Termination of Boron-Doped Diamond. *Appl. Phys. Lett.* 97 (5), 052103. doi:10.1063/1.3476346
- Honda, K., Rao, T. N., Tryk, D. A., Fujishima, A., Watanabe, M., Yasui, K., et al. (2000). Electrochemical Characterization of the Nanoporous Honeycomb Diamond Electrode as an Electrical Double-Layer Capacitor. *J. Electrochem. Soc.* 147 (2), 659. doi:10.1149/1.1393249
- Honda, K., Rao, T. N., Tryk, D. A., Fujishima, A., Watanabe, M., Yasui, K., et al. (2001). Impedance Characteristics of the Nanoporous Honeycomb Diamond Electrodes for Electrical Double-Layer Capacitor Applications. *J. Electrochem. Soc.* 148 (7), A668. doi:10.1149/1.1373450
- Hong, S.-C., Kim, S., Jang, W.-J., Han, T.-H., Hong, J.-P., Oh, J.-S., et al. (2014). Supercapacitor Characteristics of Pressurized RuO<sub>2</sub>/carbon Powder as Binder-free Electrodes. *RSC Adv.* 4 (89), 48276–48284. doi:10.1039/C4RA06370H
- Jeong, J.-H., Park, J. W., Lee, D. W., Baughman, R. H., and Kim, S. J. (2019). Electrodeposition of  $\alpha$ -MnO<sub>2</sub>/ $\gamma$ -MnO<sub>2</sub> on Carbon Nanotube for Yarn Supercapacitor. *Sci. Rep.* 9 (1), 1–8. doi:10.1038/s41598-019-47744-x
- Wang, J., He, Z., Tan, X., Wang, T., Liu, L., He, X., et al. (2020a). High-performance 2.6 V Aqueous Symmetric Supercapacitor Based on Porous Boron-Doped Diamond via Regrowth of Diamond Nanoparticles. *Carbon* 160, 71–79. doi:10.1016/j.carbon.2020.01.004
- Jiang, D.-e., Jin, Z., and Wu, J. (2011). Oscillation of Capacitance inside Nanopores. *Nano Lett.* 11 (12), 5373–5377. doi:10.1021/nl202952d
- Keskinen, J., Sivonen, E., Jussila, S., Bergelin, M., Johansson, M., Vaari, A., et al. (2012). Printed Supercapacitors on Paperboard Substrate. *Electrochimica Acta* 85, 302–306. doi:10.1016/j.electacta.2012.08.076
- Kim, H., Hong, J., Park, K.-Y., Kim, H., Kim, S.-W., and Kang, K. (2014). Aqueous Rechargeable Li and Na Ion Batteries. *Chem. Rev.* 114 (23), 11788–11827. doi:10.1021/cr500232y
- Kondo, T., Lee, S., Honda, K., and Kawai, T. (2009). Conductive Diamond Hollow Fiber Membranes. *Electrochem. Commun.* 11 (8), 1688–1691. doi:10.1016/j.elecom.2009.06.027
- Kondo, T., Kodama, Y., Ikezoe, S., Yajima, K., Aikawa, T., and Yuasa, M. (2014). Porous Boron-Doped Diamond Electrodes Fabricated via Two-step Thermal Treatment. *Carbon* 77, 783–789. doi:10.1016/j.carbon.2014.05.082
- Kondo, T., Yajima, K., Kato, T., Okano, M., Terashima, C., Aikawa, T., et al. (2017). Hierarchically Nanostructured Boron-Doped Diamond Electrode Surface. *Diam. Relat. Mater.* 72, 13–19. doi:10.1016/j.diamond.2016.12.004
- Kovalenko, I., Bucknall, D. G., and Yushin, G. (2010). Detonation Nanodiamond and Onion-Like-Carbon-Embedded Polyaniline for Supercapacitors. *Adv. Funct. Mat.* 20 (22), 3979–3986. doi:10.1002/adfm.201000906
- Lin, T., Chen, I.-W., Liu, F., Yang, C., Bi, H., Xu, F., et al. (2015). Nitrogen-doped Mesoporous Carbon of Extraordinary Capacitance for Electrochemical Energy Storage. *Science* 350 (6267), 1508–1513. doi:10.1126/science.aab3798
- Liu, T., and Li, Y. (2020). Addressing the Achilles' Heel of Pseudocapacitive Materials: Long-term Stability. *InfoMat* 2 (5), 807–842. doi:10.1002/inf2.12105
- Liu, Y., Zhou, H., Zhou, W., Meng, S., Qi, C., Liu, Z., et al. (2021). Biocompatible, High-Performance, Wet-Adhesive, Stretchable All-Hydrogel Supercapacitor Implant Based on PANI@rGO/Mxenes Electrode and Hydrogel Electrolyte. *Adv. Energy Mat.* 11 (30), 2101329. doi:10.1002/aenm.202101329
- Martin, H. B., Argoitia, A., Landau, U., Anderson, A. B., and Angus, J. C. (1996). Hydrogen and Oxygen Evolution on Boron-Doped Diamond Electrodes. *J. Electrochem. Soc.* 143 (6), L133–L136. doi:10.1149/1.1836901
- Martínez-Casillas, D. C., Mascorro-Gutiérrez, I., Arreola-Ramos, C. E., Villafán-Vidales, H. I., Arancibia-Bulnes, C. A., Ramos-Sánchez, V. H., et al. (2019). A Sustainable Approach to Produce Activated Carbons from Pecan Nutshell Waste for Environmentally Friendly Supercapacitors. *Carbon* 148, 403–412. doi:10.1016/j.carbon.2019.04.017
- Masuda, H., Yanagishita, T., Yasui, K., Nishio, K., Yagi, I., Rao, T. N., et al. (2001). Synthesis of Well-Aligned Diamond Nanocylinders. *Adv. Mat.* 13 (4), 247–249. doi:10.1002/1521-4095(200102)13:4<247::AID-ADMA247>3.0.CO;2-H
- May, P. W., Clegg, M., Silva, T. A., Zanin, H., Fatibello-Filho, O., Celorrio, V., et al. (2016). Diamond-coated 'black Silicon' as a Promising Material for High-Surface-Area Electrochemical Electrodes and Antibacterial Surfaces. *J. Mat. Chem. B* 4 (34), 5737–5746. doi:10.1039/C6TB01774F
- Ohashi, T., Sugimoto, W., and Takasu, Y. (2009). Catalytic Roughening of Surface Layers of BDD for Various Applications. *Electrochimica Acta* 54 (22), 5223–5229. doi:10.1016/j.electacta.2009.04.021
- Ohashi, T., Zhang, J., Takasu, Y., and Sugimoto, W. (2011). Steam Activation of Boron Doped Diamond Electrodes. *Electrochimica Acta* 56 (16), 5599–5604. doi:10.1016/j.electacta.2011.04.005
- Olivo, J., Brunelli, D., and Benini, L. (2010). "A Kinetic Energy Harvester with Fast Start-Up for Wearable Body-Monitoring Sensors," in Proceeding of the 2010 4th International Conference on Pervasive Computing Technologies for Healthcare, June 2010 (IEEE), 1–7. doi:10.4108/icst.pervasivehealth2010.8814
- Pandey, A., Allos, F., Hu, A. P., and Budgett, D. (2011). "Integration of Supercapacitors into Wirelessly Charged Biomedical Sensors," in Proceeding of the 2011 6th IEEE Conference on Industrial Electronics and Applications, Beijing, China, June 2011 (IEEE), 56–61. doi:10.1109/iciea.2011.5975550
- Patel, M., and Wang, J. (2010). Applications, Challenges, and Prospective in Emerging Body Area Networking Technologies. *IEEE Wirel. Commun.* 17 (1), 80–88. doi:10.1109/MWC.2010.5416354
- Patnaik, S. G., Shamsudeen Seenath, J., Bourrier, D., Prabhudev, S., Guay, D., and Pech, D. (2020). Porous RuO<sub>x</sub>NySz Electrodes for Microsupercapacitors and Microbatteries with Enhanced Areal Performance. *ACS Energy Lett.* 6 (1), 131–139. doi:10.1021/acseenergylett.0c02017
- Petrák, V., Vlčková Živcová, Z., Krýsová, H., Frank, O., Zukal, A., Klimša, L., et al. (2017). Fabrication of Porous Boron-Doped Diamond on SiO<sub>2</sub> Fiber Templates. *Carbon* 114, 457–464. doi:10.1016/j.carbon.2016.12.012
- Pilon, L., Wang, H., and d'Entremont, A. (2015). Recent Advances in Continuum Modeling of Interfacial and Transport Phenomena in Electric Double Layer Capacitors. *J. Electrochem. Soc.* 162 (5), A5158–A5178. doi:10.1149/2.0211505jes
- Portet, C., Yushin, G., and Gogotsi, Y. (2007). Electrochemical Performance of Carbon Onions, Nanodiamonds, Carbon Black and Multiwalled Nanotubes in Electrical Double Layer Capacitors. *Carbon* 45 (13), 2511–2518. doi:10.1016/j.carbon.2007.08.024
- Ramanavicius, S., and Ramanavicius, A. (2021). Charge Transfer and Biocompatibility Aspects in Conducting Polymer-Based Enzymatic Biosensors and Biofuel Cells. *Nanomaterials* 11 (2), 371. doi:10.3390/nano11020371
- Raravikar, N., Dobos, A., Narayanan, E., Grandhi, T. S. P., Mishra, S., Rege, K., et al. (2017). Investigation into Pseudo-capacitance Behavior of Glycoside-Containing Hydrogels. *ACS Appl. Mat. Interfaces* 9 (4), 3554–3561. doi:10.1021/acsami.6b11113
- Shao, Y., El-Kady, M. F., Wang, L. J., Zhang, Q., Li, Y., Wang, H., et al. (2015). Graphene-based Materials for Flexible Supercapacitors. *Chem. Soc. Rev.* 44 (11), 3639–3665. doi:10.1039/C4CS00316K
- Shi, C., Li, H., Li, C., Li, M., Qu, C., and Yang, B. (2015). Preparation of TiO<sub>2</sub>/boron-Doped diamond/Ta Multilayer Films and Use as Electrode Materials for Supercapacitors. *Appl. Surf. Sci.* 357, 1380–1387. doi:10.1016/j.apsusc.2015.10.006
- Shi, C., Li, C., Li, M., Li, H., Dai, W., Wu, Y., et al. (2016). Fabrication of Porous Boron-Doped Diamond Electrodes by Catalytic Etching under Hydrogen-Argon Plasma. *Appl. Surf. Sci.* 360, 315–322. doi:10.1016/j.apsusc.2015.11.028
- Shige Wang, S., Yang, X., Zhou, L., Li, J., and Chen, H. (2020). 2D Nanostructures beyond Graphene: Preparation, Biocompatibility and Biodegradation Behaviors. *J. Mat. Chem. B* 8 (15), 2974–2989. doi:10.1039/C9TB02845E
- Silva, L. M. d., Santos, M. d., Baldan, M. R., Beloto, A. F., and Ferreira, N. G. (2015). Boron Doped Ultrananocrystalline Diamond Films on Porous Silicon: Morphological, Structural and Electrochemical Characterizations. *Mat. Res.* 18, 1407–1413. doi:10.1590/1516-1439.002715
- Sim, H. J., Choi, C., Lee, D. Y., Kim, H., Yun, J.-H., Kim, J. M., et al. (2018). Biomolecule Based Fiber Supercapacitor for Implantable Device. *Nano Energy* 47, 385–392. doi:10.1016/j.nanoen.2018.03.011

- Simon, P., and Gogotsi, Y. (2008). Materials for Electrochemical Capacitors. *Nat. Mater* 7 (11), 845–854. doi:10.1038/nmat2297
- Simon, P., and Gogotsi, Y. (2013). Capacitive Energy Storage in Nanostructured Carbon-Electrolyte Systems. *Acc. Chem. Res.* 46 (5), 1094–1103. doi:10.1021/ar200306b
- Sinha, P., and Kar, K. K. (2020). “Introduction to Supercapacitors,” in *Handbook of Nanocomposite Supercapacitor Materials II* (Springer), 1–28. doi:10.1007/978-3-030-52359-6\_1
- Siuzdak, K., and Bogdanowicz, R. (2018). Nano-engineered Diamond-based Materials for Supercapacitor Electrodes: A Review. *Energy Technol.* 6 (2), 223–237. doi:10.1002/ente.201700345
- Yu, S., Yang, N., Vogel, M., Mandal, S., Williams, O. A., Jiang, S., et al. (2018). Battery-like Supercapacitors from Vertically Aligned Carbon Nanofiber Coated Diamond: Design and Demonstrator. *Adv. Energy Mat.* 8 (12), 1702947. doi:10.1002/aenm.201702947
- Spataru, N., Zhang, X., Spataru, T., Tryk, D. A., and Fujishima, A. (2008). Anodic Deposition of RuO<sub>2</sub>·nH<sub>2</sub>O at Conductive Diamond Films and Conductive Diamond Powder for Electrochemical Capacitors. *J. Electrochem. Soc.* 155 (1), D73. doi:10.1149/1.2804379
- Tong, W., Fox, K., Zamani, A., Turnley, A. M., Ganesan, K., Ahnood, A., et al. (2016). Optimizing Growth and Post Treatment of Diamond for High Capacitance Neural Interfaces. *Biomaterials* 104, 32–42. doi:10.1016/j.biomaterials.2016.07.006
- Torfs, T., Leonov, V., Van Hoof, C., and Gyselinckx, B. (2006). “Body-heat Powered Autonomous Pulse Oximeter,” in *Proceeding of the SENSORS, 2006 IEEE*, Daegu, Korea, Oct. 2006 (IEEE), 427–430. doi:10.1109/icsens.2007.355497
- Toupin, M., Brousse, T., and Bélanger, D. (2004). Charge Storage Mechanism of MnO<sub>2</sub> Electrode Used in Aqueous Electrochemical Capacitor. *Chem. Mat.* 16 (16), 3184–3190. doi:10.1021/cm049649j
- Trouillon, R., and O’Hare, D. (2010). Comparison of Glassy Carbon and Boron Doped Diamond Electrodes: Resistance to Biofouling. *Electrochimica Acta* 55 (22), 6586–6595. doi:10.1016/j.electacta.2010.06.016
- Turcheniuk, K., and Mochalin, V. N. (2017). Biomedical Applications of Nanodiamond (Review). *Nanotechnology* 28 (25), 252001. doi:10.1088/1361-6528/aa6ae4
- Vlčková Živcová, Z., Mortet, V., Taylor, A., Zukal, A., Frank, O., and Kavan, L. (2018). Electrochemical Characterization of Porous Boron-Doped Diamond Prepared Using SiO<sub>2</sub> Fiber Template. *Diam. Relat. Mater.* 87, 61–69. doi:10.1016/j.diamond.2018.05.007
- Wang, Q., Plylahan, N., Shelke, M. V., Devarapalli, R. R., Li, M., Subramanian, P., et al. (2014). Nanodiamond Particles/reduced Graphene Oxide Composites as Efficient Supercapacitor Electrodes. *Carbon* 68, 175–184. doi:10.1016/j.carbon.2013.10.077
- Wang, W., Liu, W., Zeng, Y., Han, Y., Yu, M., Lu, X., et al. (2015). A Novel Exfoliation Strategy to Significantly Boost the Energy Storage Capability of Commercial Carbon Cloth. *Adv. Mat.* 27 (23), 3572–3578. doi:10.1002/adma.201500707
- Wang, S., Zhou, L., Zheng, Y., Li, L., Wu, C., Yang, H., et al. (2019). Synthesis and Biocompatibility of Two-Dimensional Biomaterials. *Colloids Surfaces A Physicochem. Eng. Aspects* 583, 124004. doi:10.1016/j.colsurfa.2019.124004
- Williams, O. A. (2011). Nanocrystalline Diamond. *Diam. Relat. Mater.* 20 (5–6), 621–640. doi:10.1016/j.diamond.2011.02.015
- Xiao, J., Zhan, H., Wang, X., Xu, Z.-Q., Xiong, Z., Zhang, K., et al. (2020). Electrolyte Gating in Graphene-Based Supercapacitors and its Use for Probing Nanoconfined Charging Dynamics. *Nat. Nanotechnol.* 15 (8), 683–689. doi:10.1038/s41565-020-0704-7
- Yu, X., Yun, S., Yeon, J. S., Bhattacharya, P., Wang, L., Lee, S. W., et al. (2018a). Emergent Pseudocapacitance of 2D Nanomaterials. *Adv. Energy Mat.* 8 (13), 1702930. doi:10.1002/aenm.2017029310.1002/aenm.201702930
- Yamada, T., Uezono, T., Sugawara, H., Okada, K., Masu, K., Oki, A., et al. (2004). “Battery-less Wireless Communication System through Human Body for In-Vivo Healthcare Chip,” in *Proceeding of the Digest of Papers. 2004 Topical Meeting on Silicon Monolithic Integrated Circuits in RF Systems*, Atlanta, GA, USA, Sept. 2004 (IEEE), 322–325.
- Yang, K.-H., and Narayan, R. J. (2019). Biocompatibility and Functionalization of Diamond for Neural Applications. *Curr. Opin. Biomed. Eng.* 10, 60–68. doi:10.1016/j.cobme.2019.03.002
- Yang, N., Foord, J. S., and Jiang, X. (2016). Diamond Electrochemistry at the Nanoscale: A Review. *Carbon* 99, 90–110. doi:10.1016/j.carbon.2015.11.061
- Wang, Y., Wang, H., Xuan, J., and Leung, D. Y. C. (2020b). Powering Future Body Sensor Network Systems: A Review of Power Sources. *Biosens. Bioelectron.* 166, 112410. doi:10.1016/j.bios.2020.112410
- Yoshimura, M., Honda, K., Uchikado, R., Kondo, T., Rao, T. N., Tryk, D., et al. (2001). Electrochemical Characterization of Nanoporous Honeycomb Diamond Electrodes in Non-aqueous Electrolytes. *Diam. Relat. Mat.* 10 (3–7), 620–626. doi:10.1016/S0925-9635(00)00381-2
- Yu, S., Yang, N., Zhuang, H., Meyer, J., Mandal, S., Williams, O. A., et al. (2015). Electrochemical Supercapacitors from Diamond. *J. Phys. Chem. C* 119 (33), 18918–18926. doi:10.1021/acs.jpcc.5b04719
- Yu, S., Yang, N., Zhuang, H., Mandal, S., Williams, O. A., Yang, B., et al. (2017). Battery-like Supercapacitors from Diamond Networks and Water-Soluble Redox Electrolytes. *J. Mat. Chem. A* 5 (4), 1778–1785. doi:10.1039/C6TA08607A
- Yu, S., Yang, N., Liu, S., and Jiang, X. (2021). Diamond Supercapacitors: Progress and Perspectives. *Curr. Opin. Solid State Mater. Sci.* 25 (3), 100922. doi:10.1016/j.cossms.2021.100922
- Yun, X., Lu, B., Xiong, Z., Jia, B., Tang, B., Mao, H., et al. (2019). Direct 3D Printing of a Graphene Oxide Hydrogel for Fabrication of a High Areal Specific Capacitance Microsupercapacitor. *RSC Adv.* 9 (50), 29384–29395. doi:10.1039/C9RA04882K
- Zeng, H., Moldovan, N., and Catausan, G. (2019). Diamond Nanofeathers. *Diam. Relat. Mater.* 91, 165–172. doi:10.1016/j.diamond.2018.11.016
- Zhan, H., Sandberg, R., Xiong, Z., Liang, Q., Xie, K., Zu, L., et al. (2020a). Multiscale Studies of Nanoconfined Charging Dynamics in Supercapacitors Bridged by Machine Learning. arXiv [preprint]. Available: <https://arxiv.org/abs/2010.08151> (Accessed March 15, 2022).
- Zhan, H., Xiong, Z., Cheng, C., Liang, Q., Liu, J. Z., and Li, D. (2020b). Solvation-Involved Nanoionics: New Opportunities from 2D Nanomaterial Laminar Membranes. *Adv. Mat.* 32 (18), 1904562. doi:10.1002/adma.201904562
- Zhuang, H., Yang, N., Fu, H., Zhang, L., Wang, C., Huang, N., et al. (2015). Diamond Network: Template-free Fabrication and Properties. *ACS Appl. Mat. Interfaces* 7 (9), 5384–5390. doi:10.1021/am508851r

**Conflict of Interest:** SP is a shareholder in iBIONICS, a company developing a diamond based retinal implant. SP is a director and shareholder of Carbon Cybernetics, a company developing a diamond and carbon fibre based neural implant. AA is a shareholder in BrainConnect Pty Ltd., an Australian startup developing physiological and neurophysiological and interventional solutions for a range of neurological disorders.

The remaining authors declare that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

**Publisher’s Note:** All claims expressed in this article are solely those of the authors and do not necessarily represent those of their affiliated organizations, or those of the publisher, the editors and the reviewers. Any product that may be evaluated in this article, or claim that may be made by its manufacturer, is not guaranteed or endorsed by the publisher.

Copyright © 2022 Chambers, Praver, Ahnood and Zhan. This is an open-access article distributed under the terms of the Creative Commons Attribution License (CC BY). The use, distribution or reproduction in other forums is permitted, provided the original author(s) and the copyright owner(s) are credited and that the original publication in this journal is cited, in accordance with accepted academic practice. No use, distribution or reproduction is permitted which does not comply with these terms.